

DTIC FILE COPY

(4)

SYNTHESIS OF ENERGETIC SINGLE PHASE AND MULTI-PHASE POLYMERS  
ANNUAL PROGRESS REPORT FOR 1989

RESEARCH SUPPORTED BY THE SDIO INNOVATIVE SCIENCE AND  
TECHNOLOGY OFFICE, MANAGED BY THE OFFICE OF NAVAL RESEARCH  
ALSO SUPPORTED BY THE OFFICE OF NAVAL RESEARCH

AD-A222 491

CONTRACTS N00014-89-WX-24052 AND N00014-89-WX-2C010

DTIC  
ELECTE  
JUN 07 1990  
S D D  
Co

H. G. ADOLPH  
L. A. NOCK  
J. M. GOLDWASSER

MARCH 1990

RESEARCH AND TECHNOLOGY DEPARTMENT  
NAVAL SURFACE WARFARE CENTER  
DAHLGREN, VA 22448 - SILVER SPRING, MD 20903-5000

REPRODUCTION IN WHOLE OR IN PART IS PERMITTED FOR  
ANY PURPOSE OF THE UNITED STATES GOVERNMENT

APPROVED FOR PUBLIC RELEASE

DISTRIBUTION STATEMENT A
Approved for public release
Distribution is unlimited

90 06 06 034

# REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION <b>UNCLASSIFIED</b>			1b. RESTRICTIVE MARKINGS None		
2a. SECURITY CLASSIFICATION AUTHORITY			3. DISTRIBUTION / AVAILABILITY OF REPORT Approved for public release; distribution unlimited		
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE					
4. PERFORMING ORGANIZATION REPORT NUMBER(S) N/A			5. MONITORING ORGANIZATION REPORT NUMBER(S) N/A		
6a. NAME OF PERFORMING ORGANIZATION Naval Surface Warfare Center		6b. OFFICE SYMBOL (If applicable) R11		7a. NAME OF MONITORING ORGANIZATION Office of the Chief of Naval Research	
6c. ADDRESS (City, State, and ZIP Code) 10901 New Hampshire Avenue Silver Spring, MD 20903-5000			7b. ADDRESS (City, State, and ZIP Code) Arlington, VA 22217		
8a. NAME OF FUNDING / SPONSORING ORGANIZATION Chief of Naval Research		8b. OFFICE SYMBOL (If applicable) Code 1132P		9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER Work requests N00014-89-WX-24052 N00014-89-WX-2C010	
8c. ADDRESS (City, State, and ZIP Code) Arlington, VA 22217			10. SOURCE OF FUNDING NUMBERS		
			PROGRAM ELEMENT NO. 61153N and	PROJECT NO.	WORK UNIT ACCESSION NO. 9R11AA/ 9R11CC
11. TITLE (Include Security Classification) Synthesis of Energetic Single Phase and Multi-Phase Polymers (U)			63222C		
12. PERSONAL AUTHOR(S) H. G. Adolph, L. A. Nock, J. M. Goldwasser					
13a. TYPE OF REPORT Annual Progress Report		13b. TIME COVERED FROM 1/1/89 TO 12/31/89		14. DATE OF REPORT (Year, Month, Day) 1990 Mar 31	
15. PAGE COUNT					
16. SUPPLEMENTARY NOTATION Reproduction in whole or in part is permitted for any purpose of the United States Government					
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)		
FIELD	GROUP	SUB-GROUP	Polymers; Copolymers; Polyformals; Nitrodiols; Fluorodiols; Block Copolymers; Thermoplastic Elastomers. <i>ms</i>		
19. ABSTRACT (Continue on reverse if necessary and identify by block number) Several polyformals of novel fluorodiols and fluoronitrodiols provided by Fluorochem, Inc. were prepared. The previously prepared polyformal of tetranitrodioxatridecanediol was obtained with a molecular weight up to 10,000. This soft block has a T <sub>g</sub> of -11°C. The synthesis of poly(azidoacetals) as potential soft blocks was initiated. The first example successfully synthesized was the polyazidoacetal of 1,6-hexanediol.  New monofunctional, isocyanate terminated hard blocks with estimated melting points of 50-100°C were synthesized, including the 1:1 adduct of docosanol and toluene diisocyanate (TDI).					
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION		
22a. NAME OF RESPONSIBLE INDIVIDUAL			22b. TELEPHONE (Include Area Code)		22c. OFFICE SYMBOL

DD FORM 1473, 84 MAR

83 APR edition may be used until exhausted.  
All other editions are obsolete

SECURITY CLASSIFICATION OF THIS PAGE

U.S. Government Printing Office: 1989-629-012

0102-LF-014-6602

UNCLASSIFIED

heneicosyl isocyanate, and the 1:1 adduct of eicosafuoroundecanol and TDI. Several energetic (nitro) diisocyanates for use in (AB)<sub>N</sub> polymer synthesis were prepared. Carbonyl chloride terminated nitro- and nitraminediols were prepared by reaction of the diols with triphosgene/pyridine for use as block linking agents.

A large number of segmented polymers containing alternative fluoro- and nitrosubstituted polyformal soft blocks and urethane hard blocks have been synthesized by the block linking approach combining -OH and -NCO terminated blocks. The properties of these (AB)<sub>N</sub> polymers depend strongly on the structure of A and B. Several of these materials were characterized by rheometric measurements (at the University of Massachusetts, Amherst) which show them to be highly viscous liquids at room temperature with quasielastic properties which gradually disappear on heating. The polymers exhibit no sharp melting transitions by DSC analysis. In contrast, a series of ABA polymers synthesized by the same approach and containing a short hydrocarbon (C<sub>22</sub>) hard (A) block and a nitropolyformal soft (B) block show well-defined melting/crystallization transitions in the DSC. Elastomeric properties in the temperature range of 0-45°C were exhibited by these polymers when the M<sub>N</sub> of the soft block was about 10,000 or higher. The melt viscosities of the polymers increased with increasing molecular weight of the soft block, especially when TDI was used for chain extension of the soft block before the block linking step. End-capping of poly(AMMO) (M<sub>w</sub> ≈ 6200) with docosanol/TDI and eicosafuoroundecanol/TDI hard blocks was demonstrated, but the resulting ABA polymers showed no elastomeric properties.

The previously developed method for molecular weight determination, based on gel permeation chromatography/viscometry, was validated using well characterized commercial polymers ranging in molecular weight from 1,000 to 160,000, as well as polymer mixtures. This method can now be used to accurately determine the M<sub>N</sub> of any polymer, copolymer, or polymer blend.

Specific impulse calculations show that the (AB)<sub>N</sub> block copolymers prepared in this work have specific impulses near 220.



Accession For	
NTIS CRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution	
Availability Codes	
Dist	Avail. and/or Special
A-1	

## CONTENTS

	<u>Page</u>
INTRODUCTION .....	1
RESULTS AND DISCUSSION .....	1
Homopolyformals and -acetals .....	1
Copolyformals .....	9
Energetic Diisocyanates and Other Difunctional Block Linkers .....	9
Monofunctional Hard Blocks .....	11
(AB) <sub>N</sub> Block Copolymer Synthesis .....	14
ABA Block Copolymer Synthesis .....	22
Polymer Characterization .....	35
EXPERIMENTAL SECTION .....	41
REFERENCES .....	49

## ILLUSTRATIONS

<u>Figure</u>	<u>Page</u>
1 GP Chromatogram of a Poly[octafluorotetranitrodecane-1,10-diol ( <u>1</u> ) formal] .....	2
2 GP Chromatogram of a Poly[dodecafluorotetranitrododecane-1,12-diol ( <u>2</u> ) formal] .....	3
3 GP Chromatogram of Poly[tetradecafluoroundecane-1,11-diol ( <u>3</u> ) formal] .....	5
4 GP Chromatogram of Poly[hexacosafuoroheptadecane-1,17-diol ( <u>4</u> ) formal] .....	6
5 GP Chromatogram of Poly[tetranitrotridecanediol ( <u>5</u> ) formal], M <sub>n</sub> ≈ 10,000, 60g Batch .....	7
6 GP Chromatogram of Poly(hexane-1,6-diol azidoacetal) .....	8
7 GP Chromatogram of a Poly[hexanitropentadecanediol ( <u>6</u> ) formal-co-hexane-1,6-diol formal] .....	10
8 <sup>1</sup> H NMR Spectrum of Urethane <u>14</u> .....	12
9 <sup>1</sup> H NMR Spectrum of Urethane <u>15</u> .....	13

# ILLUSTRATIONS (Con't)

<u>Figure</u>		<u>Page</u>
10	GP Chromatogram of Urethane <u>17</u> .....	15
11	$^1\text{H}$ NMR Spectrum of Urethane <u>17</u> .....	16
12	Viscosity vs. Temperature of Some $(\text{AB})_N$ Block Polymers .....	18
13	Recovered vs. Applied Strain at $30^\circ\text{C}$ for Some $(\text{AB})_N$ Block Copolymers .....	19
14	Recovered vs. Applied Strain at $50^\circ\text{C}$ for Some $(\text{AB})_N$ Block Copolymers .....	20
15	GP Chromatogram of Poly(AMMO), $\bar{M}_n = 3125$ , Chain Extended with TDI .....	21
16	$^1\text{H}$ NMR Spectrum of a Poly( <u>5</u> formal) after End-capping with TDI and Reaction with Methanol .....	23
17	GP Chromatogram of ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 9000$ , and Isocyanate <u>13</u> .....	26
18	DSC Traces for ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 9000$ , and Isocyanate <u>13</u> .....	27
19	GP Chromatogram of ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 7600$ , and Isocyanate <u>13</u> .....	28
20	GP Chromatogram of ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 7600$ , TDI, and Isocyanate <u>13</u> .....	29
21	DSC Traces for ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 7600$ , TDI, and Isocyanate <u>13</u> .....	30
22	GP Chromatogram of ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 4460$ , and Isocyanate <u>13</u> .....	31
23	GP Chromatogram of an ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 4460$ , TDI, and Isocyanate <u>13</u> (10% <u>13</u> ) .....	32
24	GP Chromatogram of an ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 4460$ , TDI, and Isocyanate <u>13</u> (8.5% <u>13</u> ) .....	33
25	GP Chromatogram of an ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 4460$ , TDI, and Isocyanate <u>13</u> (5.4% <u>13</u> ) .....	34
26	GP Chromatogram of ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 7600$ , and Octadecyl Isocyanate .....	36
27	GP Chromatogram of ABA Block Polymer from Poly( <u>5</u> formal), $\bar{M}_n \approx 7600$ , and Heneicosyl Isocyanate .....	37

# ILLUSTRATIONS (Con't)

<u>Figure</u>		<u>Page</u>
28	GP Chromatogram of Product from Poly(AMMO) and <u>13</u> .....	38
29	<sup>1</sup> H NMR Spectrum of Product from Poly(AMMO) and <u>13</u> .....	39

## TABLES

<u>Table</u>		<u>Page</u>
1	(AB) <sub>N</sub> Polymers Prepared from Polyformals of <u>5</u> by Chain Extension with OCN-R-NCO .....	17
2	Specific Impulse Calculations (PEP Code) for Some Polyformal/Urethane Block Copolymers .....	22
3	ABA Polymers by Reaction of <u>13</u> with Polyformals of <u>5</u> ; Ratio 2:1 .....	25
4	Comparison of Reported and Measured Molecular Weights for Some Standard Polymer Samples .....	40
5	Comparison of Calculated and Measured Molecular Weights for Some Polymer Mixtures .....	40

# SYNTHESIS OF ENERGETIC SINGLE PHASE AND MULTI-PHASE POLYMERS


## INTRODUCTION

The work described in this report has several objectives. One is to synthesize and characterize energetic single phase polymers (homo- and copolymers), primarily hydroxy terminated fluoro- and nitro-substituted polyformals, which may be useful as binders for cast-curable energetic compositions, and as components for multi-phase segmented (block) copolymers. The major objective is to establish the chemistry for the synthesis of block copolymers from such polydiols and other difunctional energetic polymers, and to provide methods for the characterization of the block copolymers produced. The block copolymers to be synthesized are desired to be elastomers in the temperature range of about  $-10^{\circ}$  to  $+70^{\circ}\text{C}$  and liquids at temperatures above about  $70-90^{\circ}\text{C}$ . Low melt-viscosities are desired. It is believed that such properties, if they can be achieved, will permit and facilitate continuous extrusion processing of propellants which use these polymers as binders. The first objective is supported primarily by the Office of the Chief of Naval Research, while research toward the second major objective is supported primarily by the SDI, Office of Innovative Science and Technology. The two efforts are closely related, and funding support overlaps in the area of copolymer synthesis. The results are therefore presented together.

## RESULTS AND DISCUSSION

Homopolyformals and -acetals. Some further efforts were conducted to prepare new polyformals of potential interest as soft or hard blocks for block copolymers, or to improve/scale up the preparation of polymers of demonstrated interest for this use.

The previously investigated<sup>1</sup> and unsuccessful condensation of fluoronitrodiols 1 and 2 with trioxane was revisited and conditions were identified which allowed the preparation of low molecular weight oligoformals



$$\underline{1} : n = 4$$

$$\underline{2} : n = 6$$

with the use of sulfolane and  $\text{BF}_3$  etherate. The highest  $\bar{M}_n$ s for 1 were about 1000 (82% yield), and for 2 about 1400 (73% yield). GPCs are shown in Figs. 1 and 2.

Two new, long-chain fluorodiols were obtained from Fluorochem, Inc. It was hoped that these diols (3 and 4) would form higher molecular weight polyformals and copolyformals than the shorter hexane- and heptanediols which we usually work with. This appears to be the case at least for homopolyformal

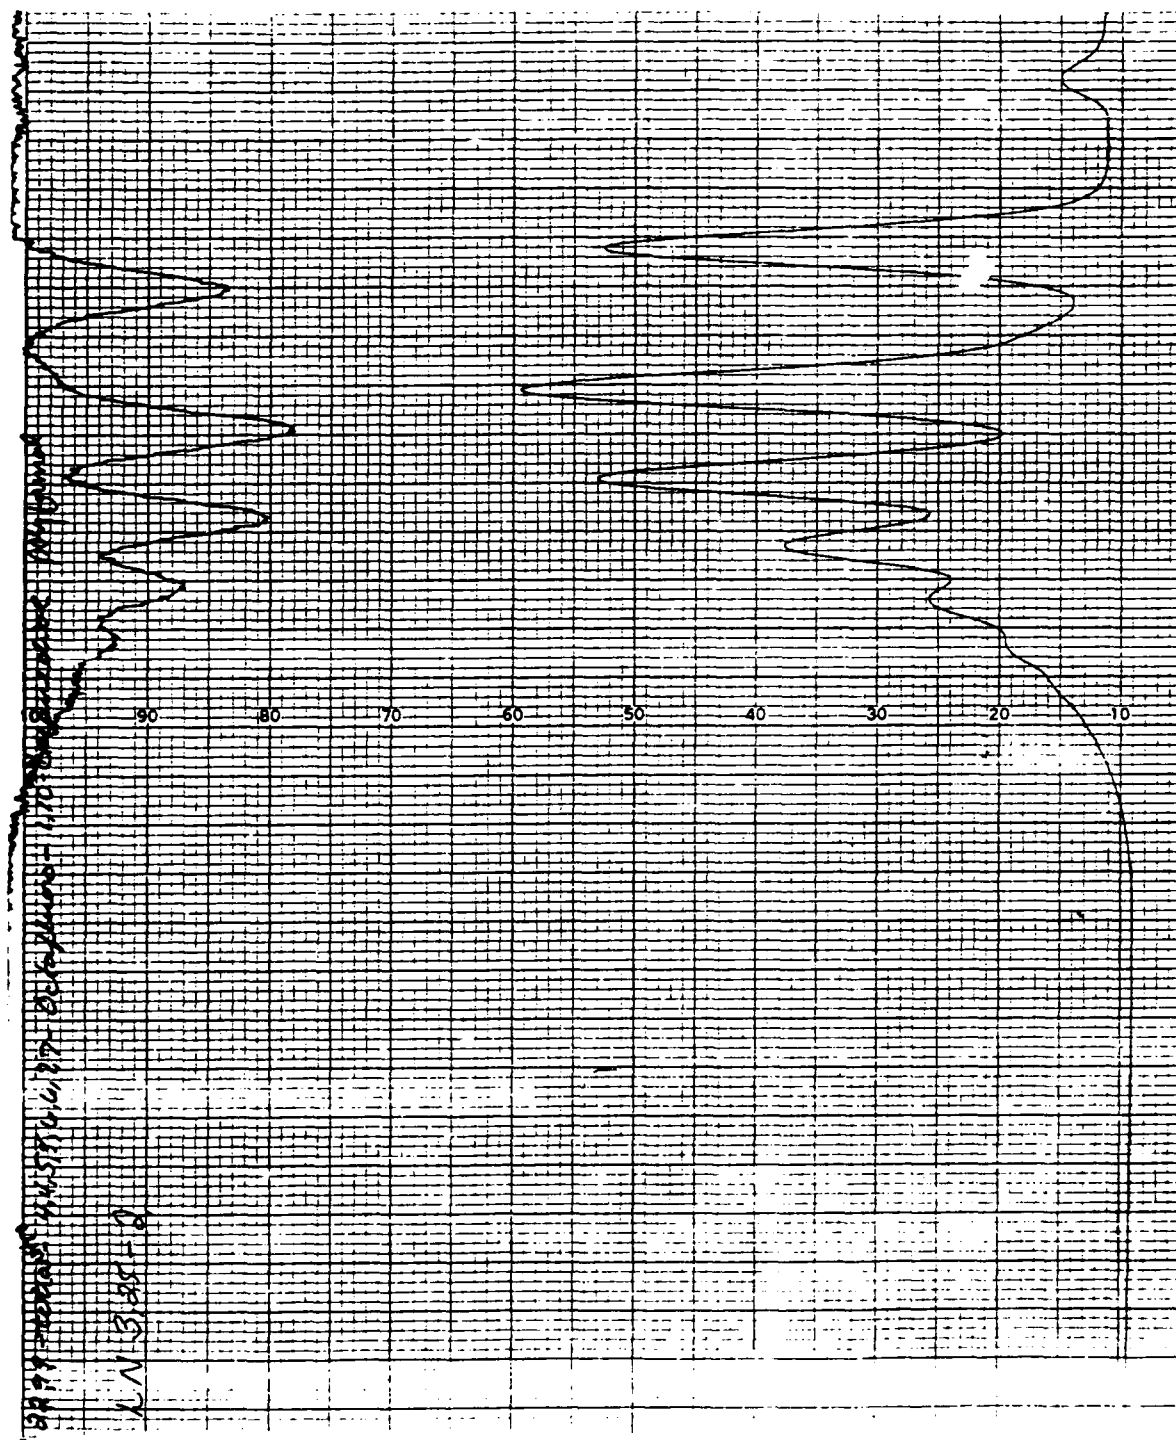


Fig. 1 GP Chromatogram of a Poly[octafluorotetranitrodecane-1,10-diol (1) formal]




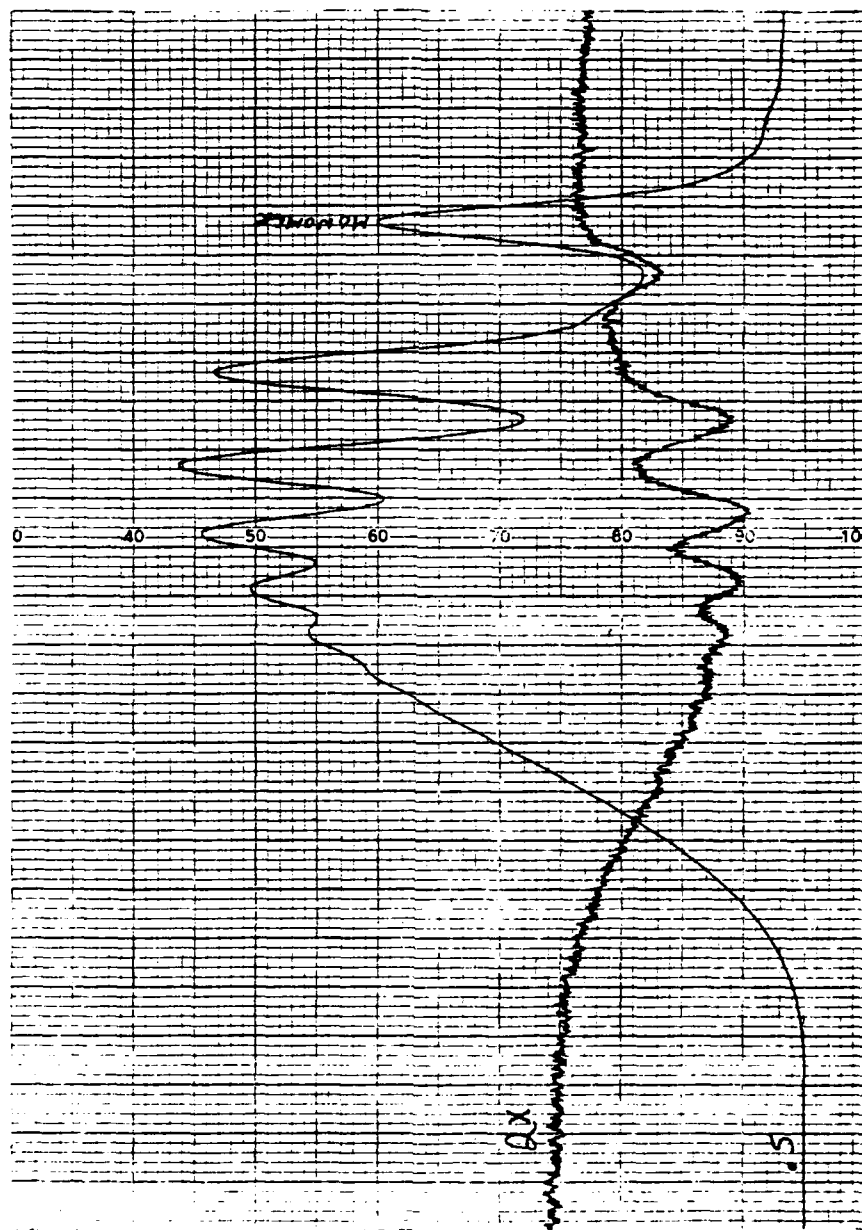


Fig. 2 GP Chromatogram of a Poly[dodecafluorotetranitrododecane-1,12-diol (2) formal]





$$\underline{3} : n = 7$$

$$\underline{4} : n = 13$$

formation: Diol 3 under the usual conditions with trioxane/sulfolane and  $\text{BF}_3$  etherate or  $\text{SnCl}_4$  gave polyformal resins with  $\bar{M}_n$  8000-9000, while 4 formed partially insoluble materials in at least the same molecular weight range. GPCs are shown in Figs. 3 and 4. It appears that particularly diol 4 may be useful for the preparation of copolyformals with nitrodiols with sufficiently high molecular weight to be useful as soft blocks for ABA polymers.


In collaboration with the NSWC 6.2 Explosives Block, the synthesis of monomers 5 and 6 was scaled up to obtain starting material for the preparation of larger quantities of block copolymers for testing. About 5 lbs of 5 was prepared at Rocketdyne, while 6 is being synthesized (1 lb) in house.



The procedure for the preparation of the high  $\bar{M}_n$  polyformal ( $\approx 10,000$ ) of the tetranitrotridecanediol 5 was optimized further to make it reproducible and provide a polymer free of low molecular weight impurities. The improved procedure was scaled up to the 60g level and is ready for production of this polymer on a larger scale. The yield of purified polymer at the 60g level was  $\approx 80\%$ ; the GPC is shown in Fig. 5.

Several attempts were made to increase the  $\bar{M}_n$  of the polyformal of 5 beyond the directly attainable 10,000: a) by further reaction of the isolated polymer with  $\text{CH}_2\text{O}/\text{SnCl}_4$ ; these attempts failed, not unexpectedly, because of the reversibility of the formal reaction; b) by chain extension with phosgene (in the form of triphosgene) and base; although this reaction worked with low  $\bar{M}_n$  polymer, it failed with the material of  $\bar{M}_n \approx 10,000$ . Chain extension with diisocyanates is possible, but alternatives not involving urethane formation are being sought.

To further decrease the glass transition temperature of polyformal soft blocks than has been possible by copolymerization of diols, the synthesis of polyacetals of nitrodiols such as 5 and 6 seemed desirable. To avoid dilution of the energy content, it was decided to attempt the synthesis of azidoacetals. As a model reaction, the polycondensation of 7 and 8 was studied. Polymer formation occurred readily in the presence of  $\text{BF}_3$  etherate in vacuo (to remove ethanol); the GP chromatogram is shown in Fig. 6. The

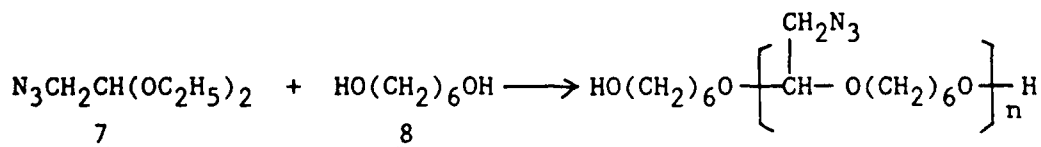

reaction will be studied further and applied to nitrodiols. Since 7 is readily accessible from commercially available bromoacetaldehyde acetal,

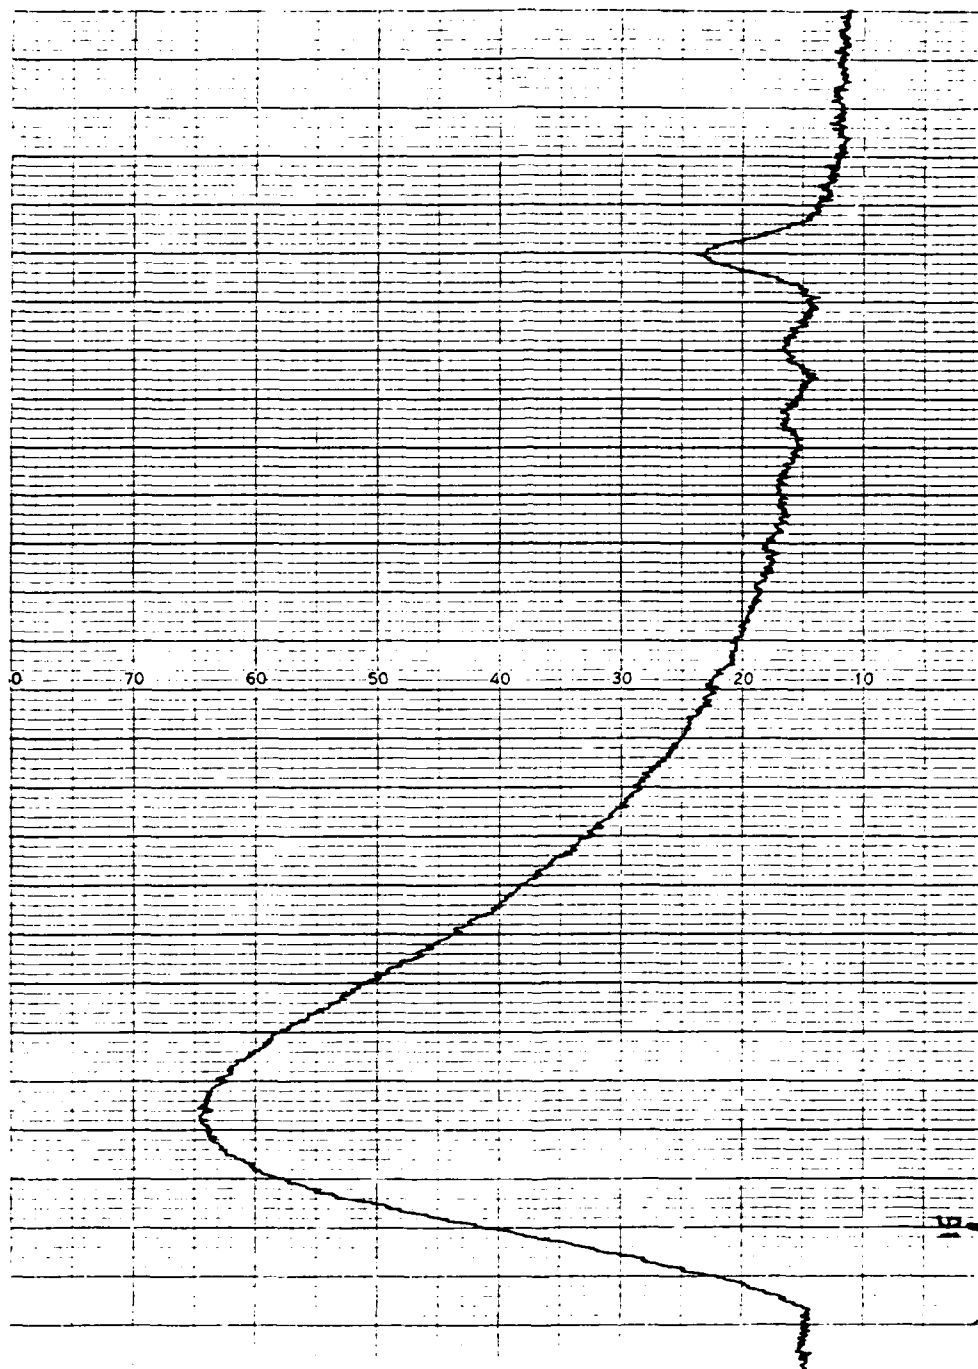


Fig. 3 GP Chromatogram of Poly[tetradecafluoroundecare-1,11-diol (3) formal]

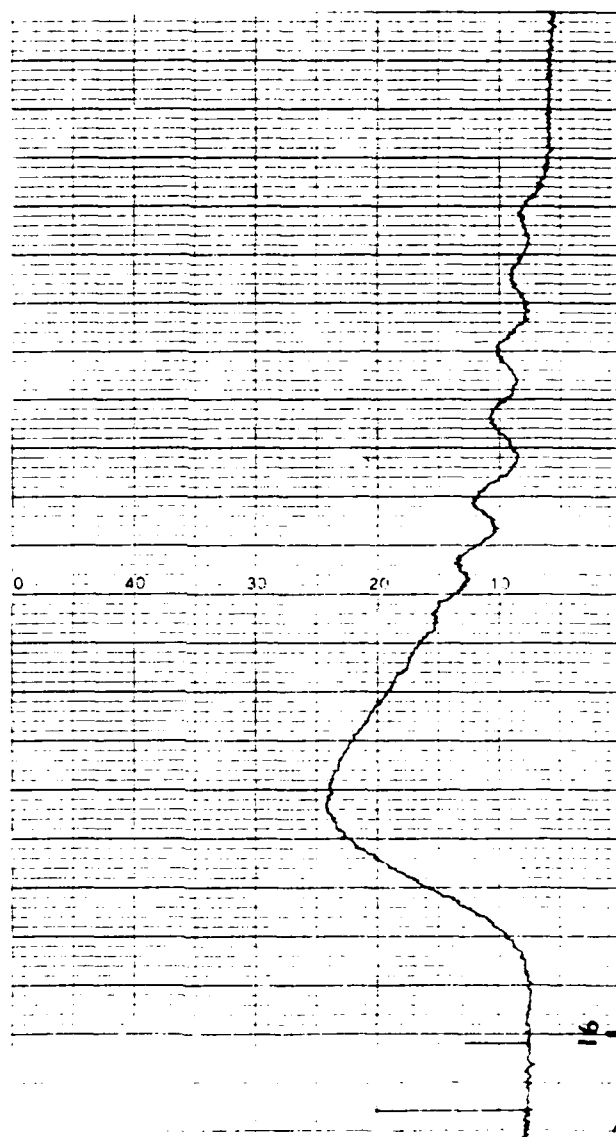


Fig. 4 GP Chromatogram of Poly[hexacosafluorohexadecane-1,17-diol (4) formal]

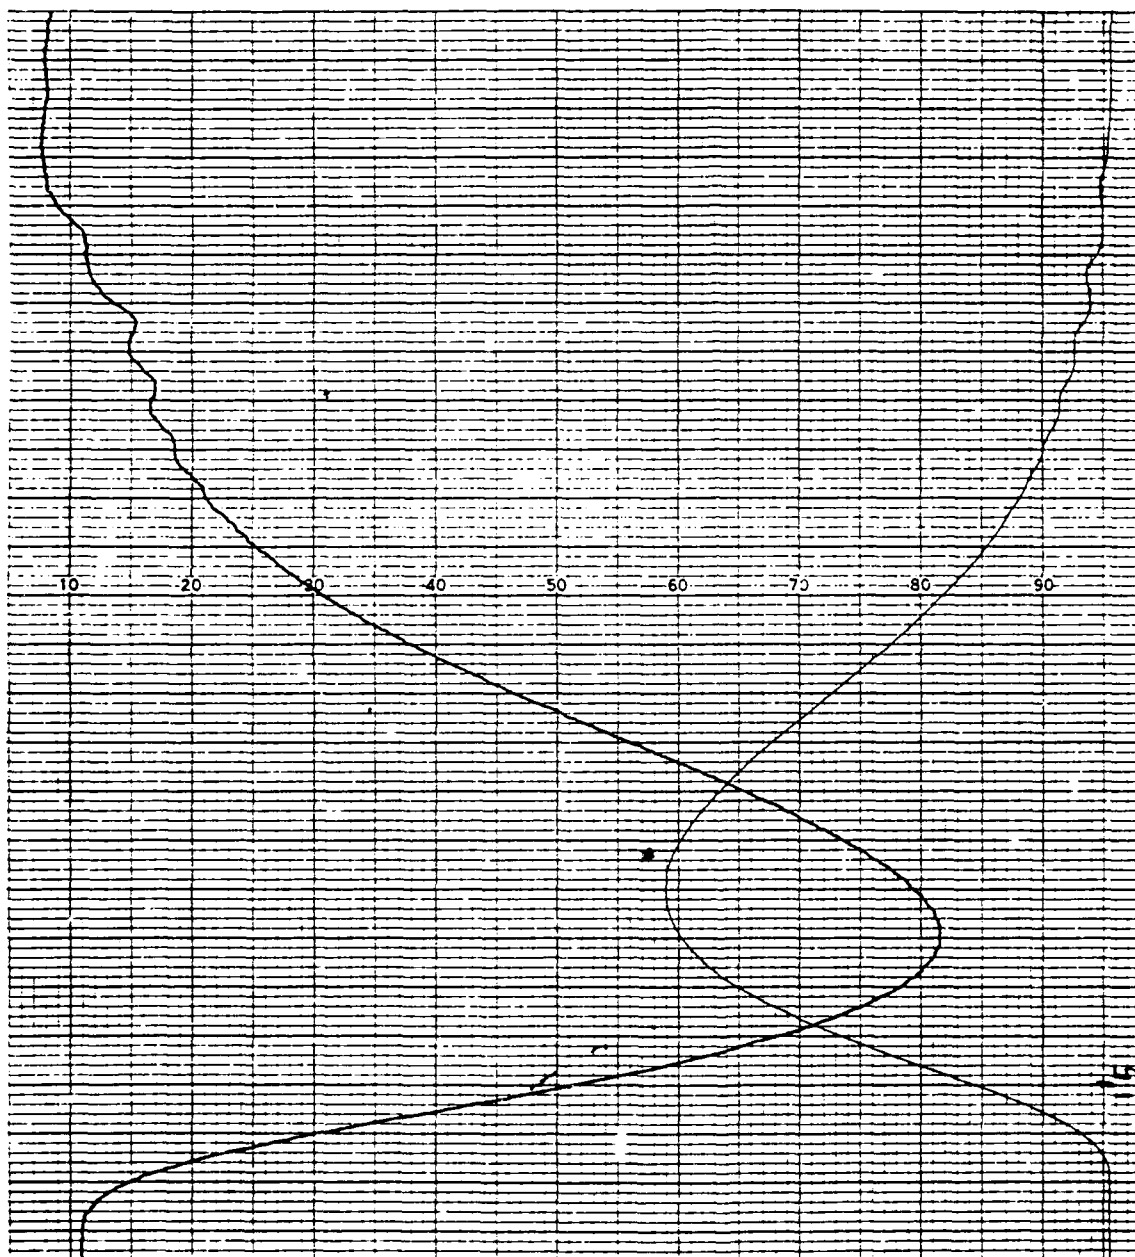


Fig. 5 GP Chromatogram of Poly[tetranitrotridecanediol (5) formal],  $\bar{M}_n \approx 10,000$ , 60g Batch


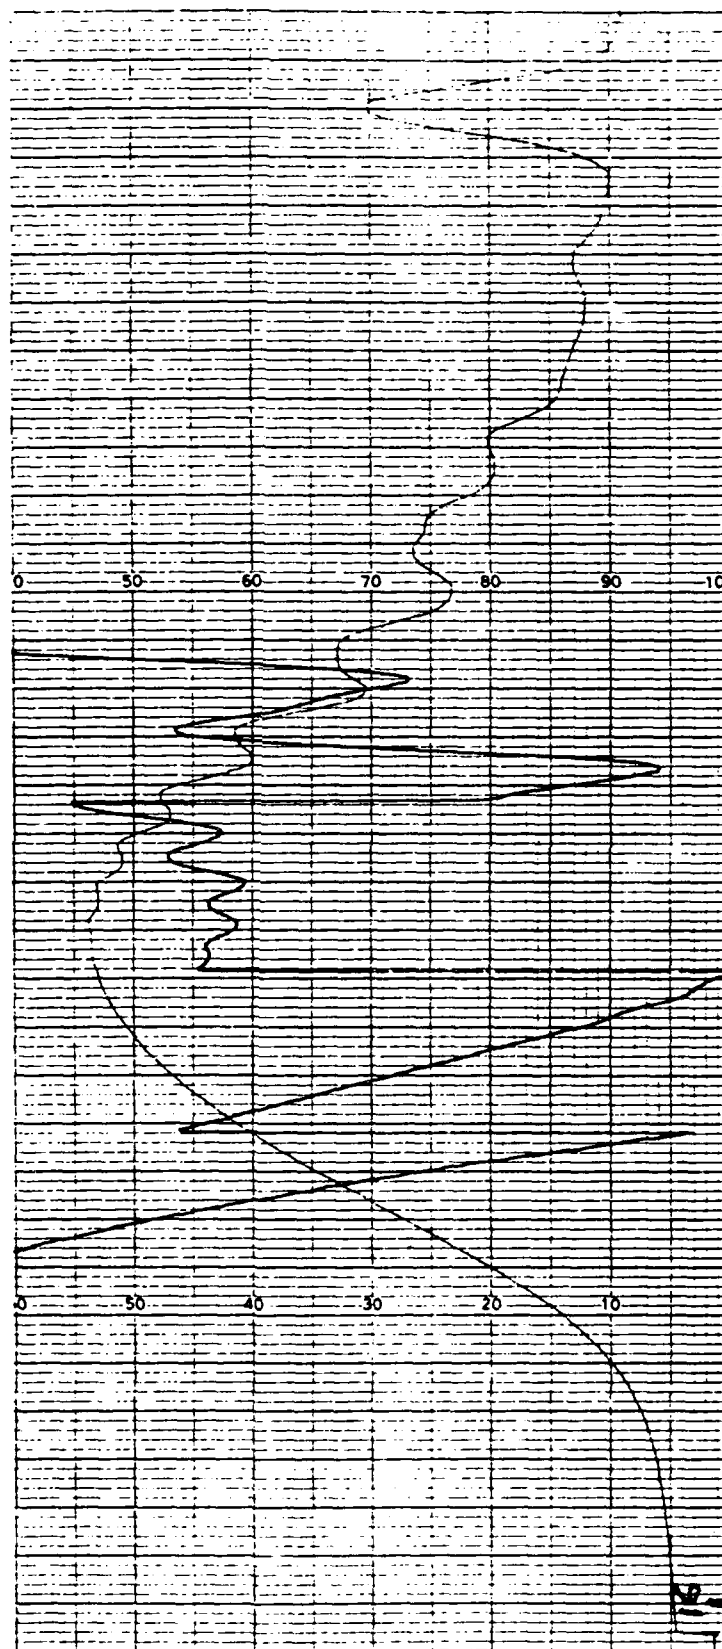


Fig. 6 GP Chromatogram of Poly(hexane-1,6-diol azidoacetal)



polyazidoacetals should be a practical class of energetic polymers.

Copolyformals.- In an effort to prepare fluorine-free polyformal soft blocks for TPE synthesis, the copolymerization of the hexanitropentadecanediol 6 with hexane-1,6-diol (8) and butane-1,4-diol (9) was pursued. A 70/30 copolyformal of 6 and 8 was readily prepared;  $M_n$  was  $\approx 2400$  (GPC, Fig. 7). Similarly, with 9 a 70/30 copolymer was obtained with  $M_n < 2000$ . The synthesis of higher molecular weight copolymers is being attempted. In addition, heptane-1,7-diol will be tried as comonomer for this purpose.

Energetic Diisocyanates and Other Difunctional Block Linkers.- The energetic diisocyanate precursor 10 was synthesized. It can be converted in situ by heating to the corresponding diisocyanate which was intended for use in making  $(AB)_N$  block copolymers, in which it functions as the hard block.

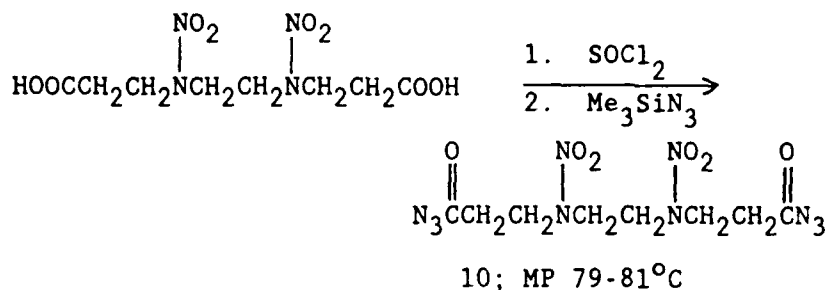

By reaction of the corresponding diols with triphosgene and pyridine, the chlorocarbonate-pyridin complexes 11 and 12 were obtained. Reaction of 11 with hexanediol gave a polyester, indicating that 11 and 12 should also be useful for making  $(AB)_N$  block copolymers.

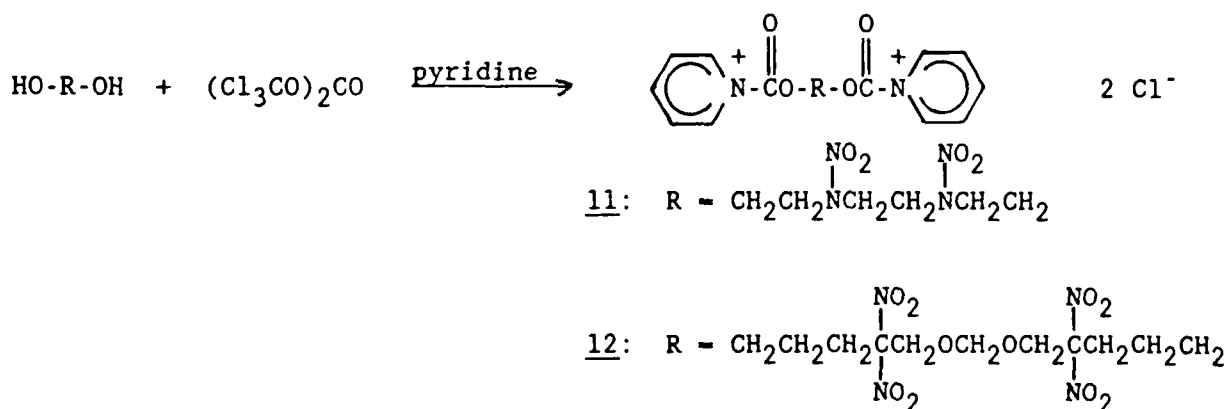


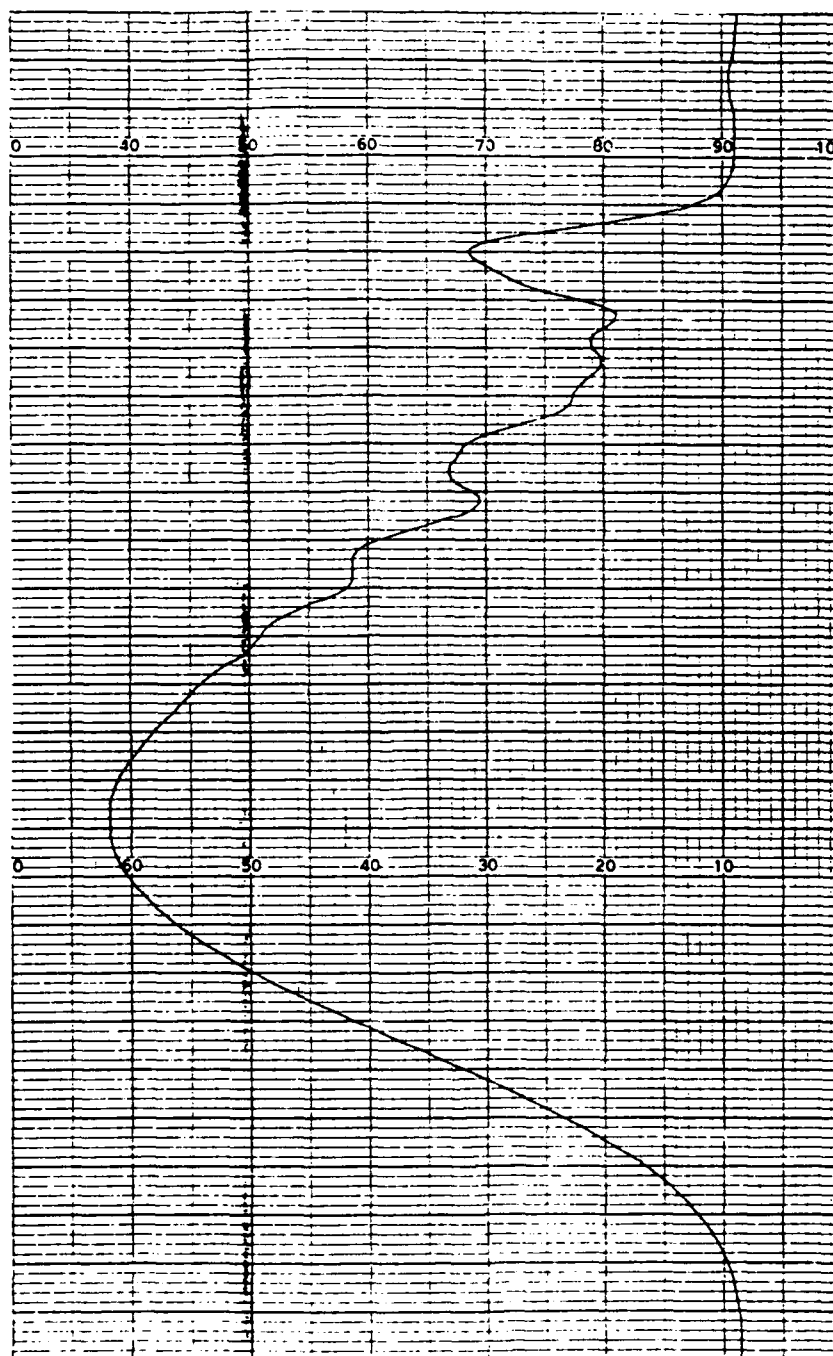



Fig. 7 GP Chromatogram of a Poly[hexanitropentadecanediol (6) formal-co-hexane-1,6-diol formal]




**Monofunctional Hard Blocks.-** Several isocyanate terminated, monofunctional "hard blocks" were prepared by reaction of monofunctional alcohols with excess TDI. These non-energetic "blocks" are intended to be used in the synthesis of ABA tri-block polymers with B being an energetic soft block such as the polyformal of 5 or poly(AMMO). Alcohols used initially were docosan-1-ol ( $R = CH_3(CH_2)_{21}$ ) which has a melting point of 65-72°C, and eicoso-1-fluoroundecanol

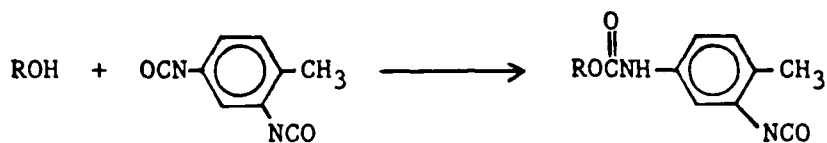

( $R = HCF_2(CF_2)_9$ ) with a melting point of 95-97°C. The isocyanate 13 was isolated as a white solid, mp 84-5°C, and stored over  $P_2O_5$  without decomposition. 13 was reacted with excess methanol to give the expected urethane 14, mp 94-6°C, whose  $^1H$  NMR spectrum (Fig. 8) integrated correctly

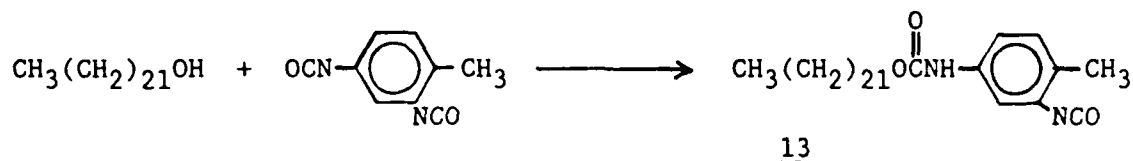


for this structure. 13 was also reacted with 5 (2:1 ratio) to give 15, mp 117-119°C, whose  $^1H$  NMR spectrum (Fig. 9) again integrated correctly for this structure. 14 and 15 showed only one peak in the GPC. Thus, the structure

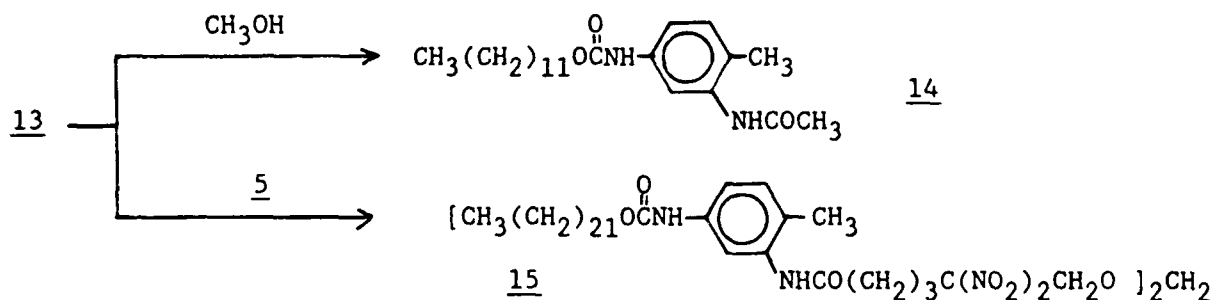

of 13 as a monofunctional, isocyanate terminated "block" seems well established.

The isocyanate 16 was similarly prepared and characterized by  $^1H$  NMR and GPC after reaction with methanol.

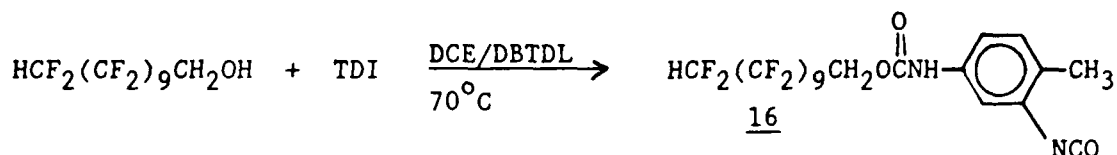

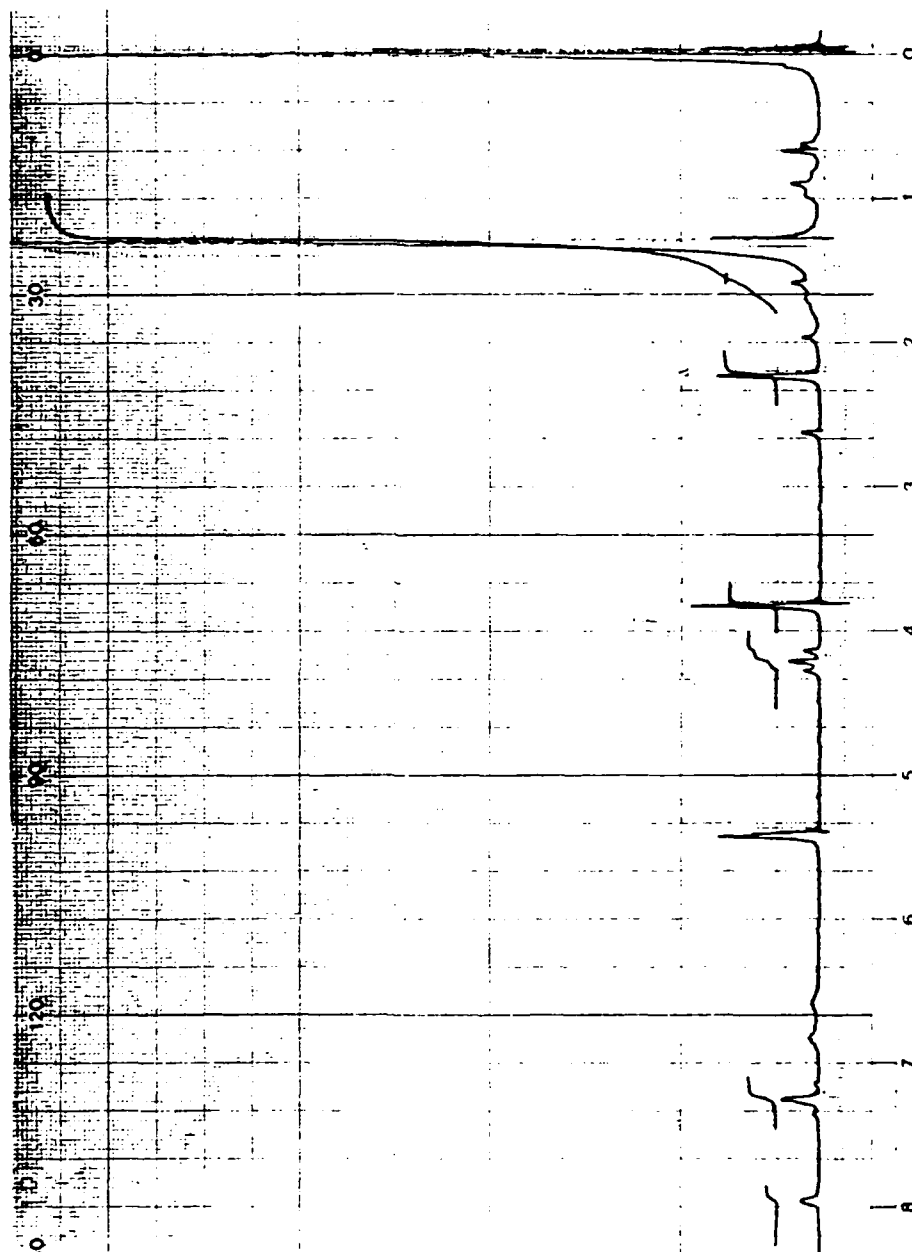


Fig. 8  $^1\text{H}$  NMR Spectrum of Urethane 14



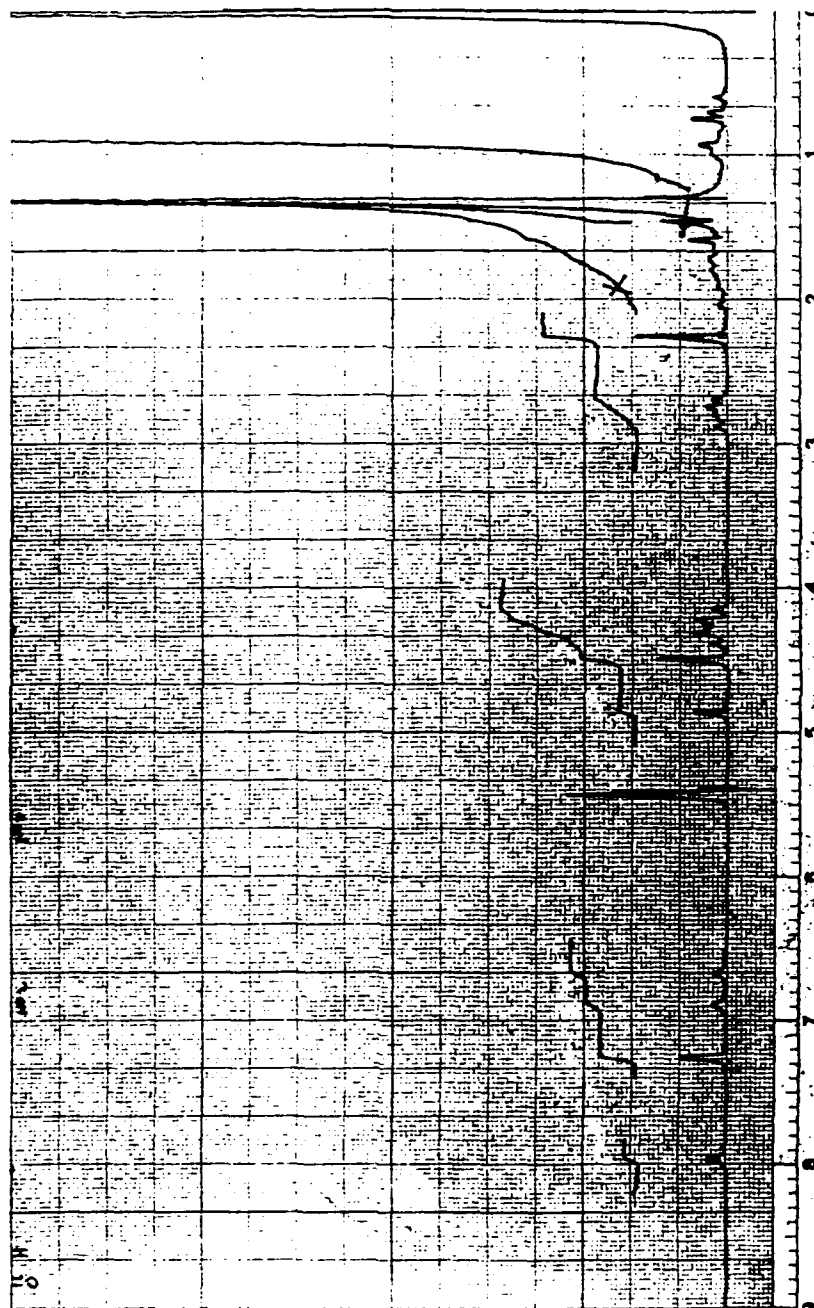


Fig. 9  $^1\text{H}$  NMR Spectrum of Urethane 15

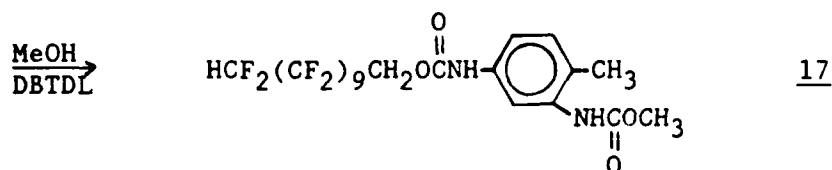


The GPC of 17 (Fig. 10) shows a small peak of higher molecular weight, but the  $^1\text{H}$  NMR spectrum (Fig. 11) integrates satisfactorily.


The structurally related isocyanate precursor 18 without the additional internal urethane moiety was prepared from docosanoic acid via the acid chloride:



The synthesis of the energetic "hard block" 19 has been initiated. Initial results indicate that the melting point of 18 is too high ( $>150^\circ\text{C}$ ), but similar structures with lower melting points can be envisioned.

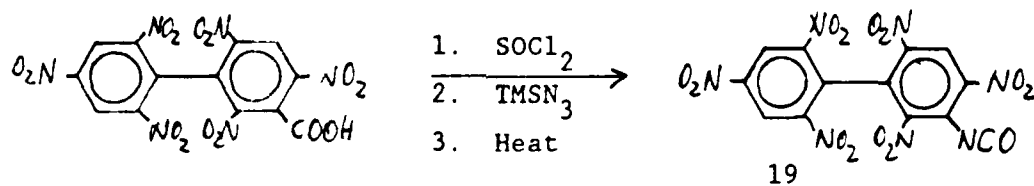

(AB)<sub>N</sub> Block Copolymer Synthesis. In the previous work,<sup>2</sup> we reported the synthesis of (AB)<sub>N</sub> block copolymers by chain extension of various polyformal "soft blocks" with diisocyanates. Some of these polymers exhibited quasi TPE



properties. Additional examples were prepared this year, by chain extension of polyformals of 5 with different molecular weights, to complete a study of properties of the resulting "block copolymers" as a function of isocyanate structure. The new polymers prepared are listed in Table 1. Prof. Chien from the University of Massachusetts arranged to have rheological characterization performed on several of these and other (AB)<sub>N</sub> polymers prepared by us.

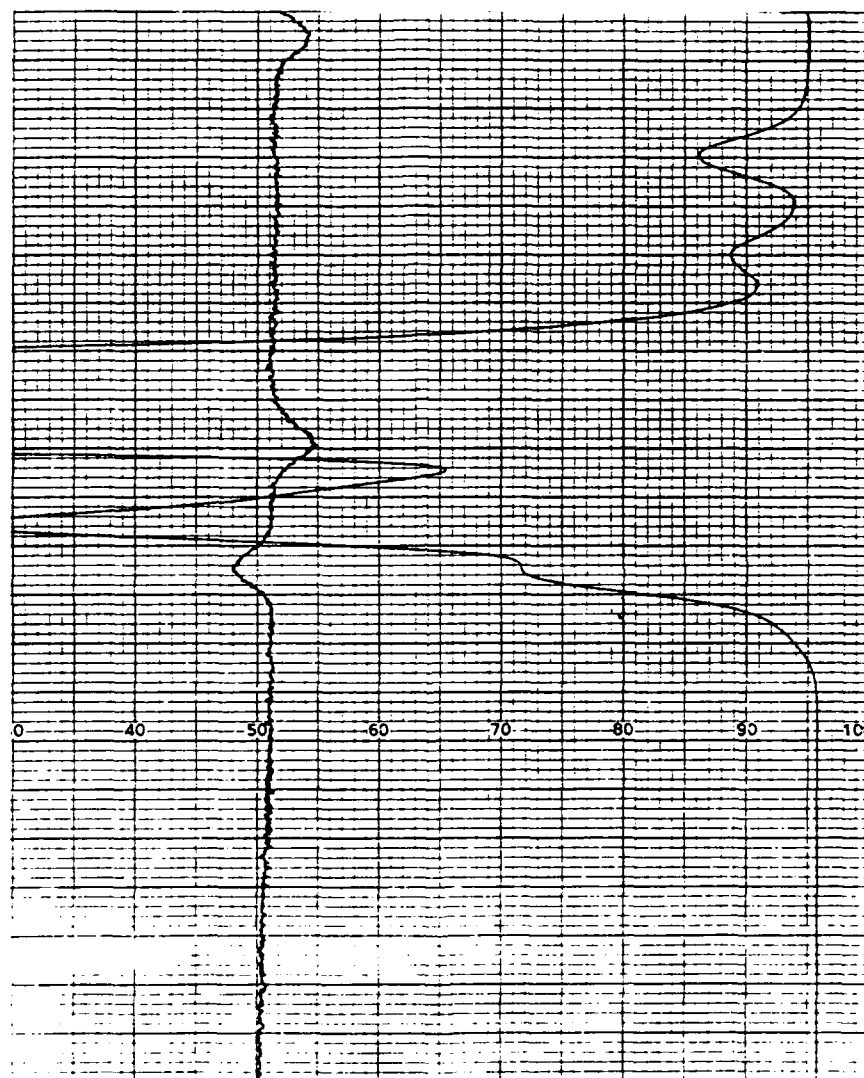


Fig. 10 GP Chromatogram of Urethane 17

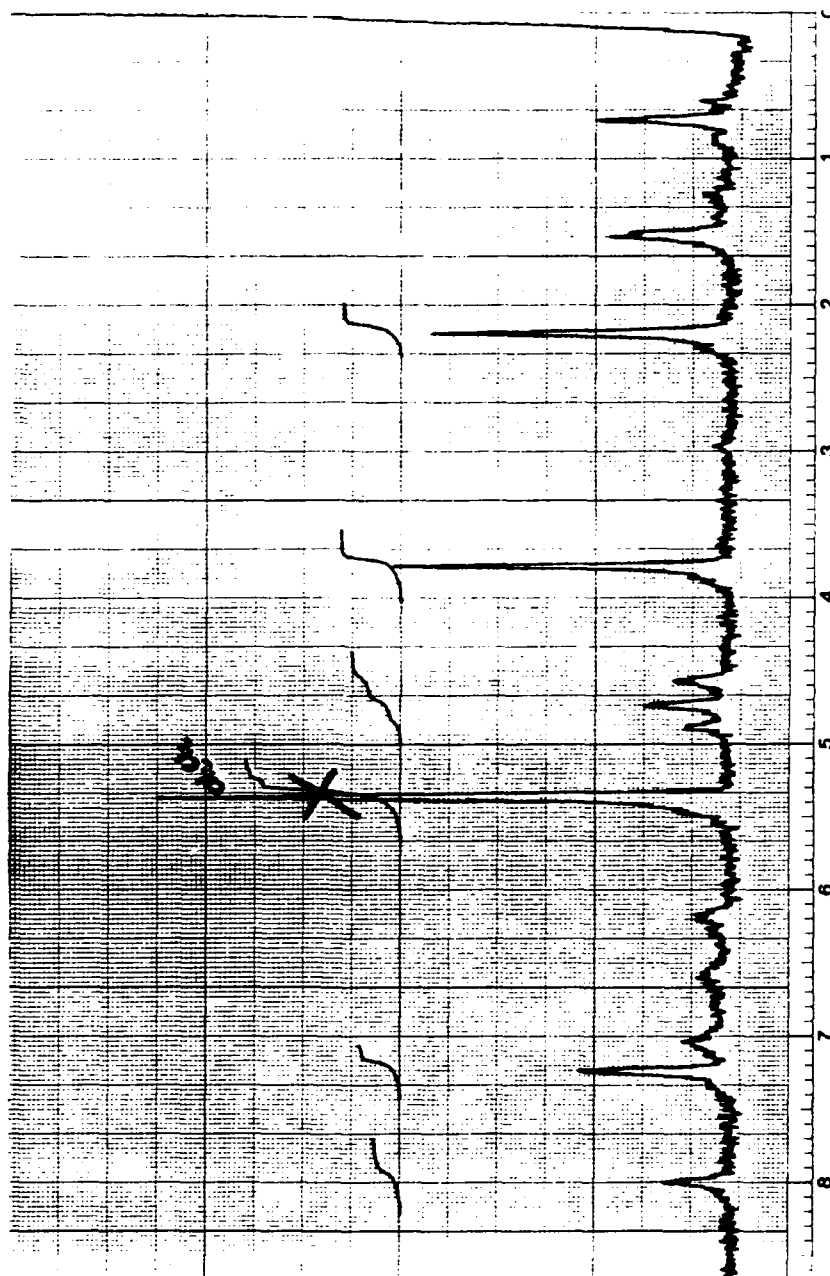



Fig. 11  $^1\text{H}$  NMR Spectrum of Urethane 17

Table 1. (AB)<sub>N</sub> Polymers Prepared from Polyformals of 5 by Chain Extension with OCN-R-NCO

$\bar{M}_n$ of <u>5</u> Polyformal	OCN-R-NCO	$\bar{M}_n$ of Product	Appearance at r.t.
4500		71,000 (GPC)	tough elastomer
7600		123,000 (GPC)	tough elastomer
4500	IPDI	50-60,000 (est'd)	soft elastomer
7600	IPDI	low	soft elastomer
7600	HMDI	≤ 30,000 (est'd)	soft elastomer

Some results of these tests are shown in Figures 12-14. They corroborate previously<sup>2</sup> reported DSC data which show no sharp melting transitions for these polymers. It can be concluded that most, if not all, of the (AB)<sub>N</sub> polymers prepared by us are not phase separated. On warming, they gradually soften and lose their elastic properties. Therefore, further work with this type of (AB)<sub>N</sub> structure is being deemphasized.

A sample of difunctional poly(AMMO), obtained from R. Wardle (Thiokol Corp.) and having a reported OH equ. wt. of 3125, was also chain-extended with TDI to give a polymer of  $\bar{M}_n \approx 25,000 - 30,000$  (GPC, Fig. 15). This material was a resin devoid of elastic properties.

Specific impulse calculations for several of the (AB)<sub>N</sub> "block copolymers" prepared by chain-extension of polyformal soft blocks were made and are shown in Table 2. The data indicate that the fluorocomonomer used for lowering of  $T_g$  has no adverse (or beneficial) effect on performance. Also included are data for GAP azide and GAP nitrate, two potential non-volatile plasticizers for energetic soft blocks in (AB)<sub>N</sub> or ABA block copolymers.

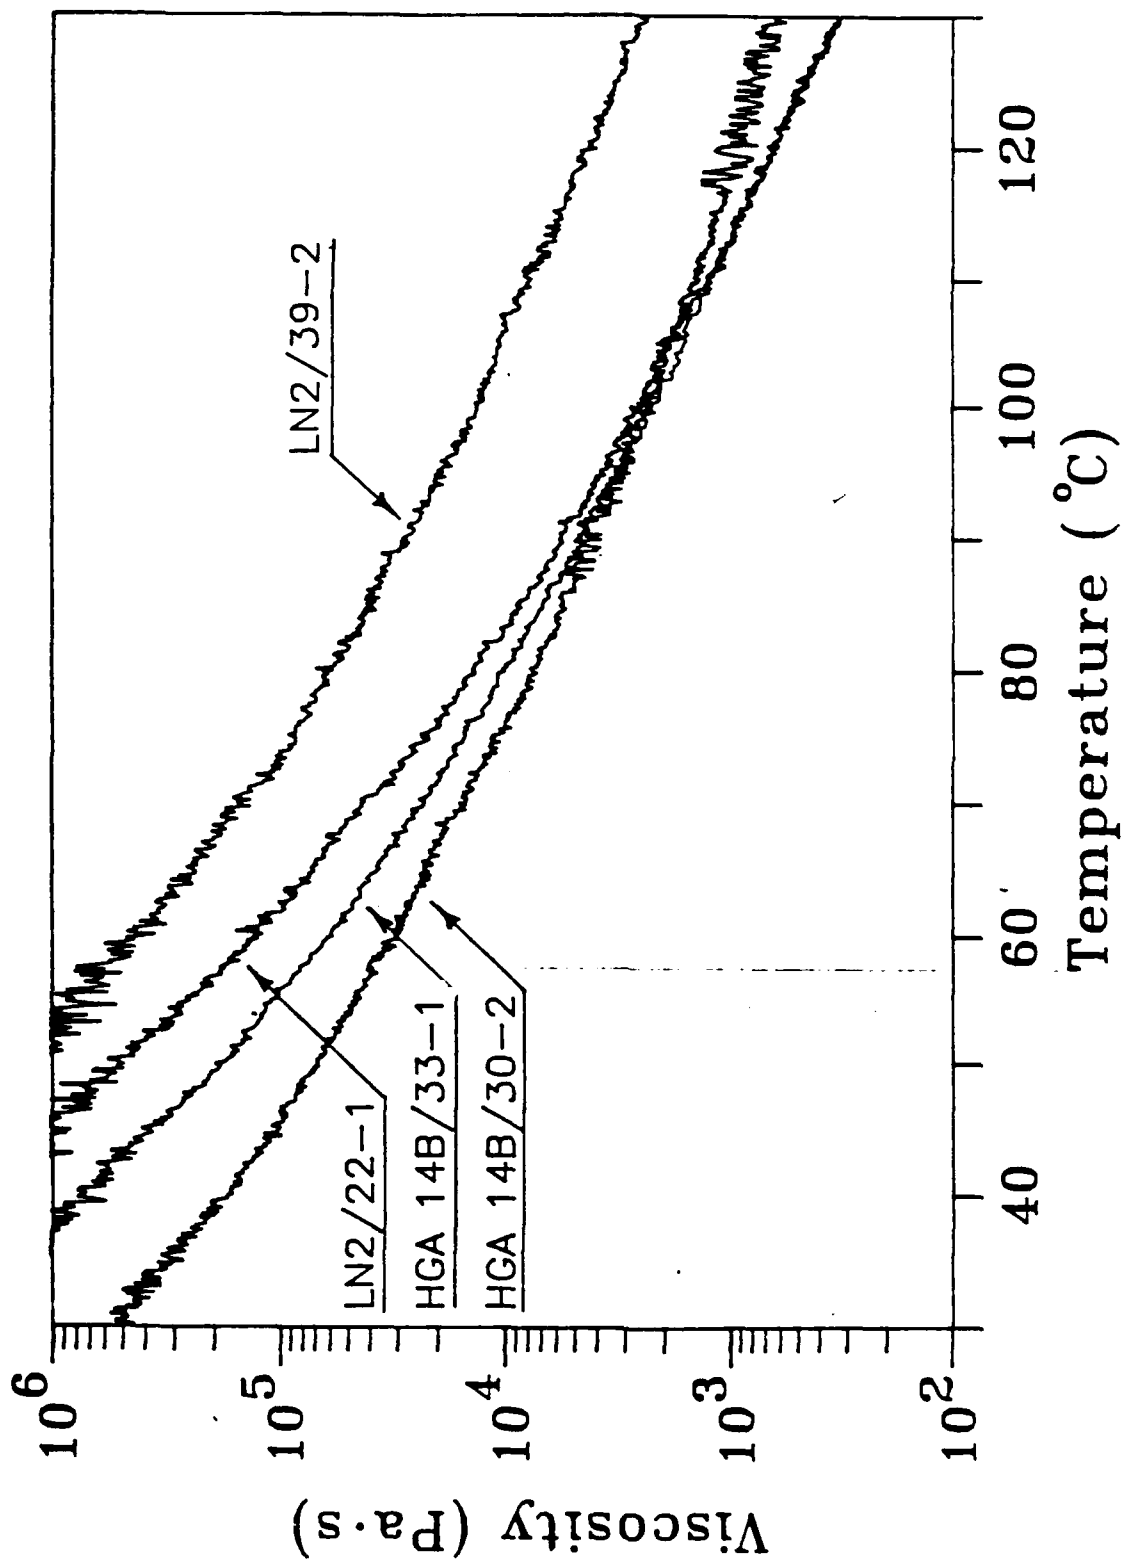


Fig. 12 Viscosity vs. Temperature of Some (AB)<sub>N</sub> Block Polymers



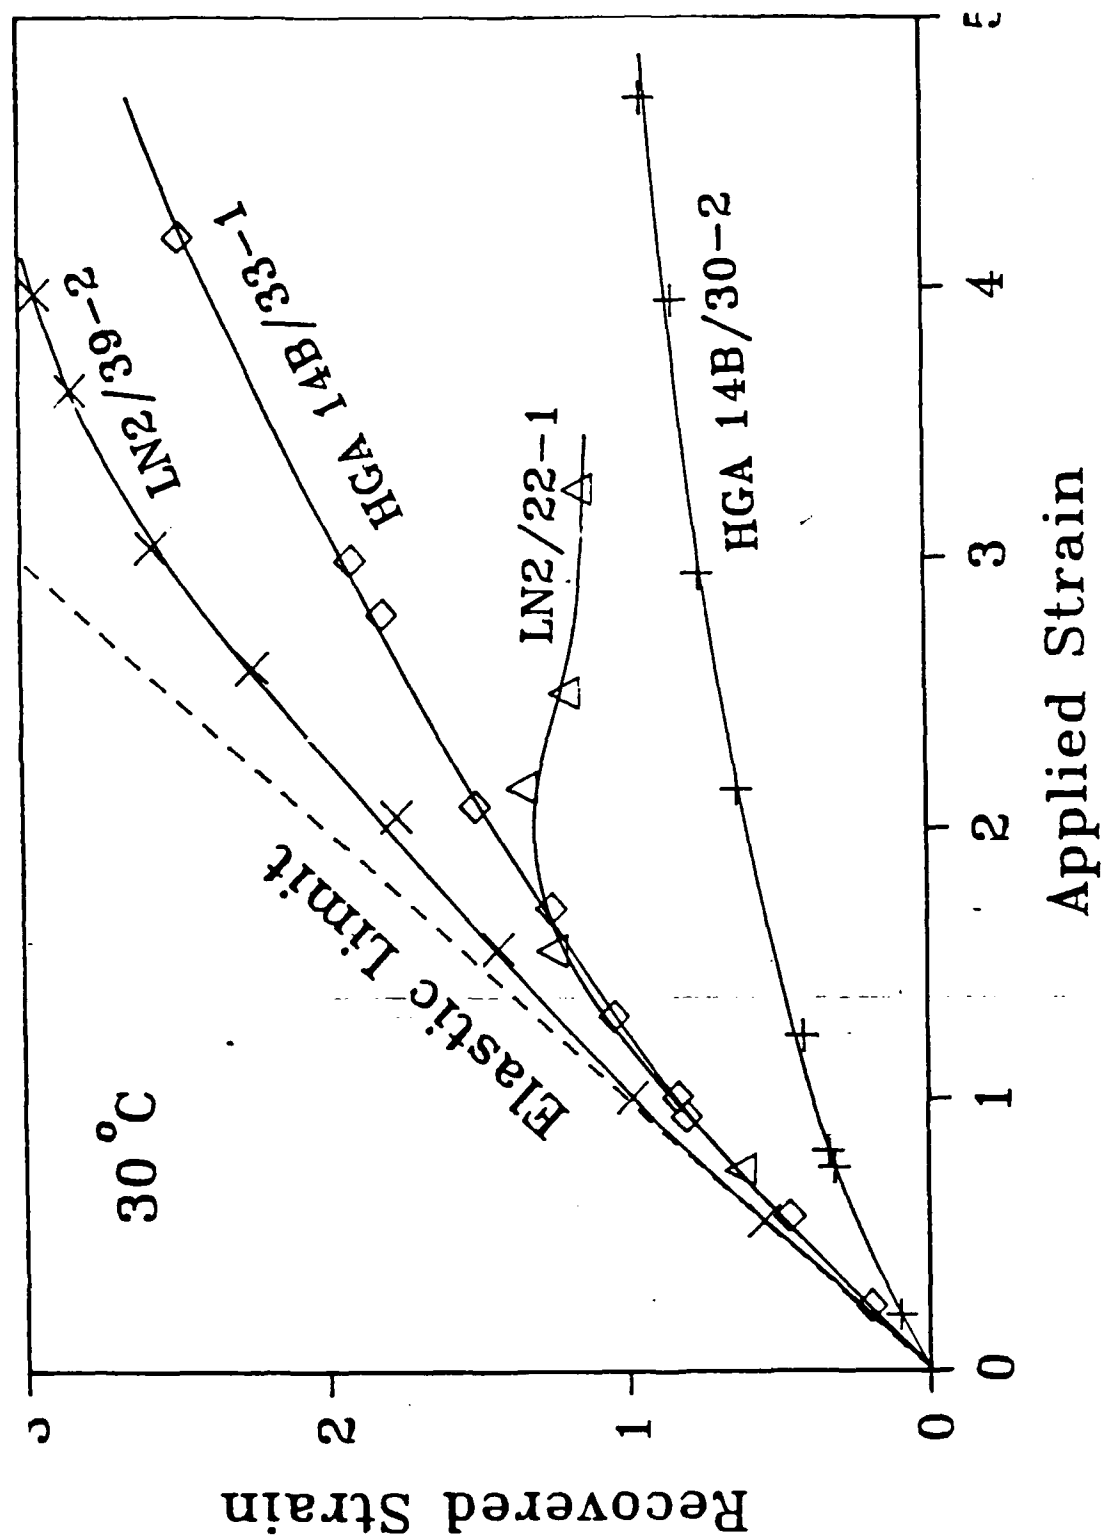


Fig. 13 Recovered vs. Applied Strain at 30°C for Some (AB)<sub>N</sub> Block Copolymers

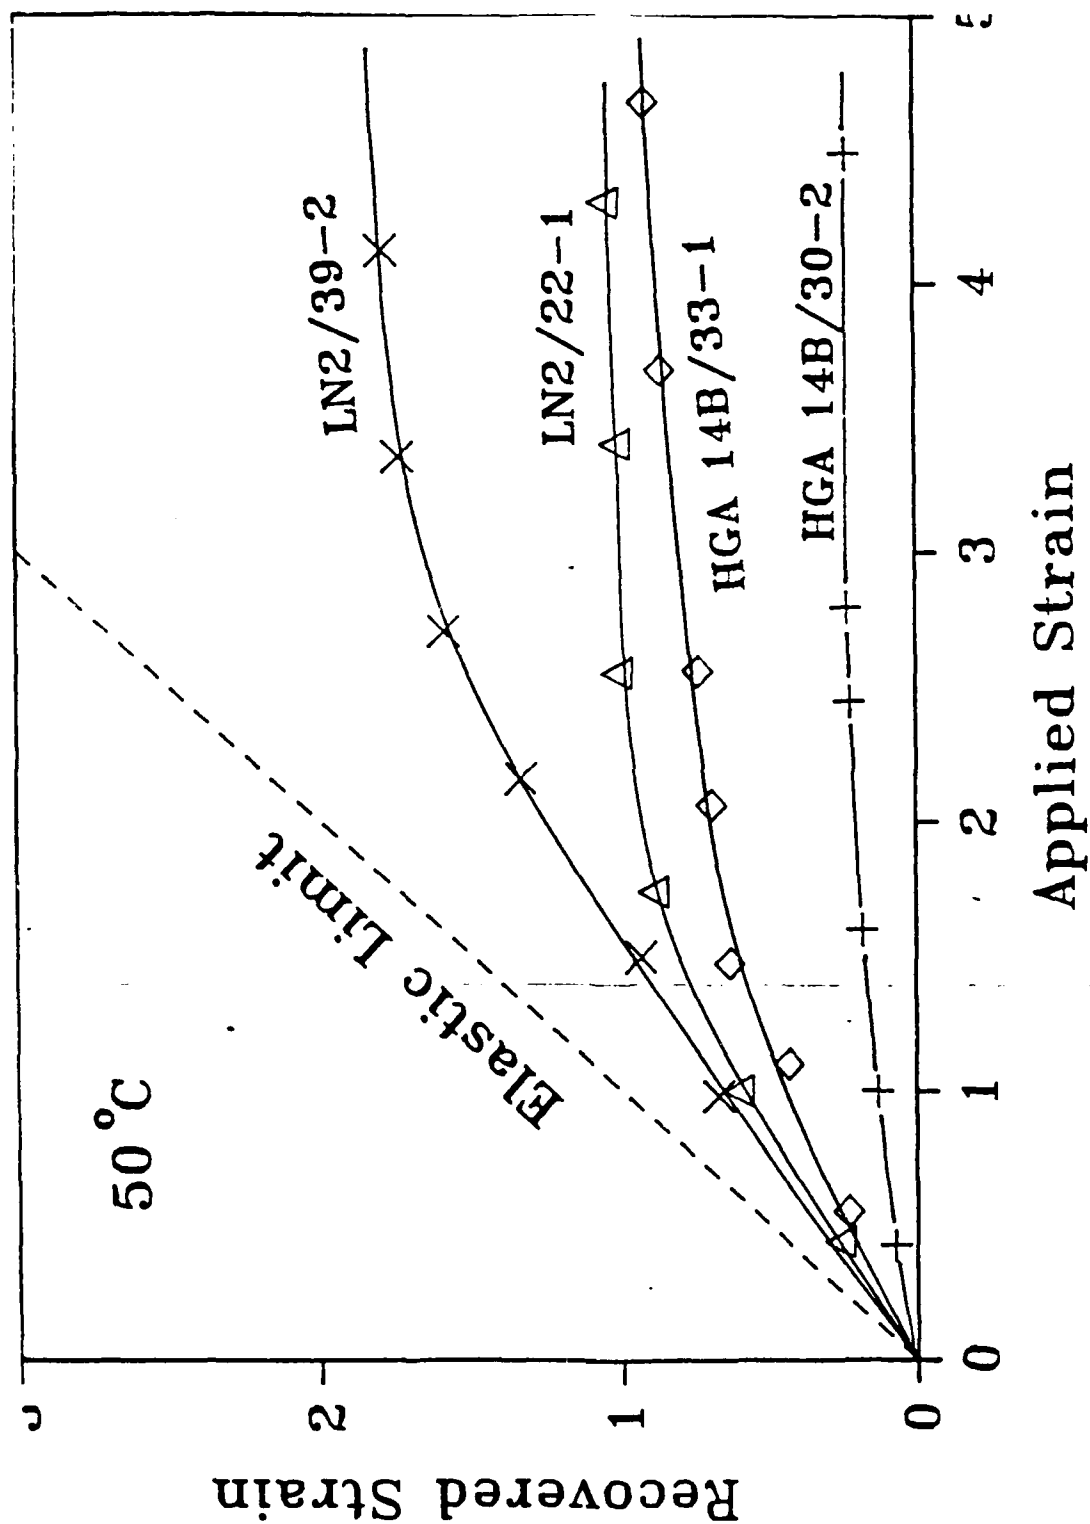


Fig. 14 Recovered vs. Applied Strain at 50°C for Some (AB)<sub>N</sub> Block Copolymers

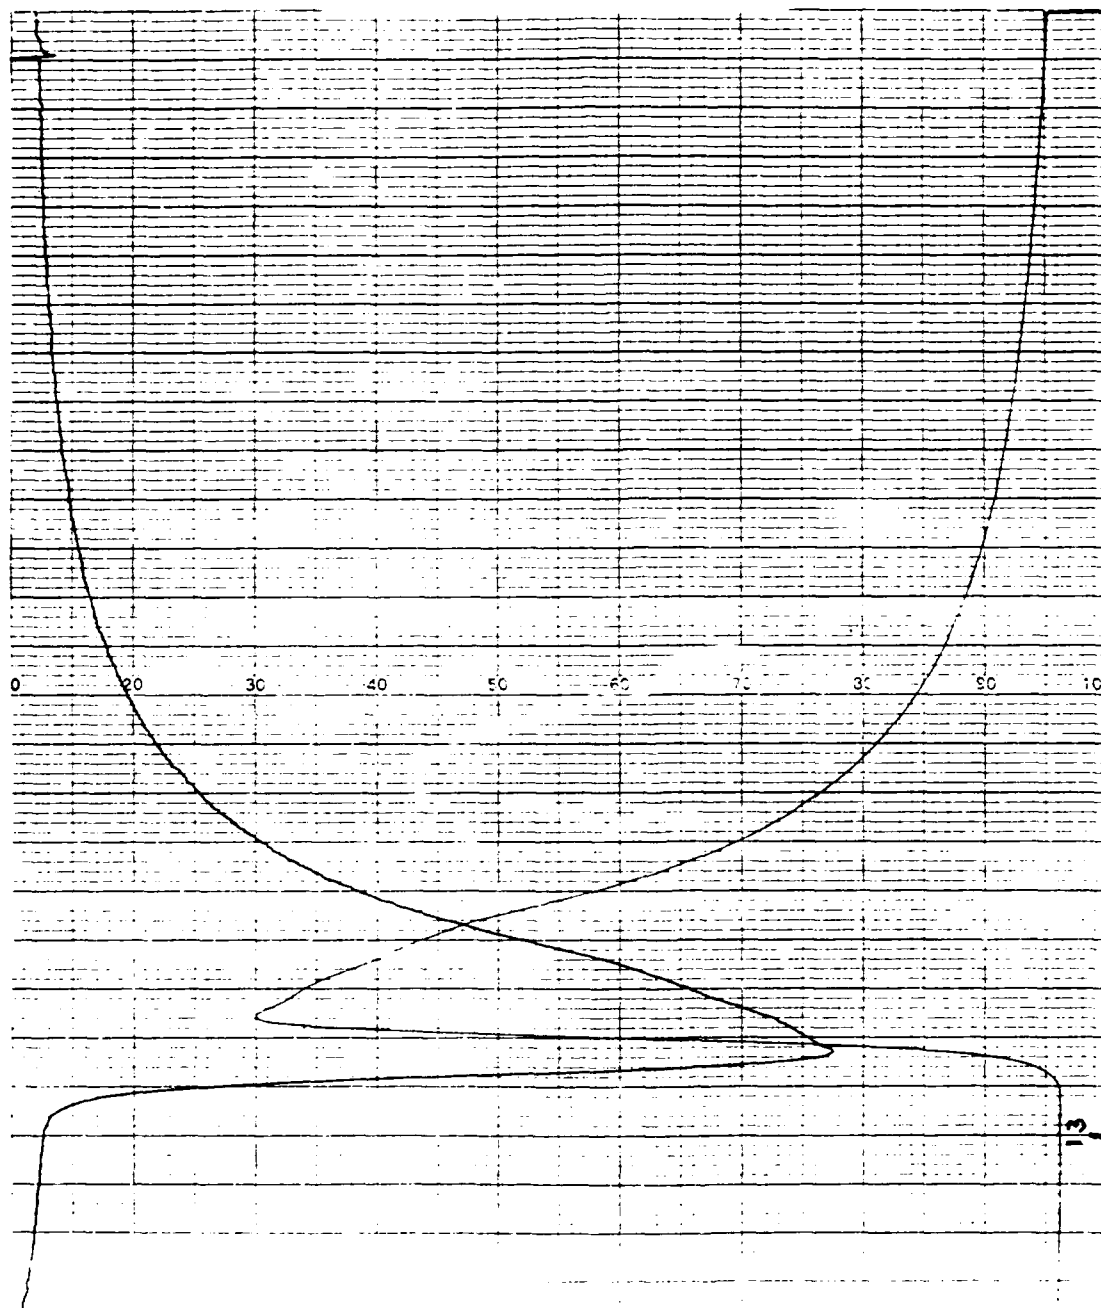


Fig. 15 GPC Chromatogram of Poly(AMMO),  $\bar{M}_n = 3125$ , Chain Extended with TDI

Table 2. Specific Impulse Calculations (PEP Code) for Some Polyformal/Urethane Block Copolymers

COMPOSITION*	H <sub>F</sub> ** (cal/g)	D** (g/cm <sup>3</sup> )	I <sub>sp</sub>	D-I <sub>sp</sub>	P <sub>J</sub> Kbar
<u>5</u> POLYFORMAL/TDI	-196	1.35	222.5	300.3	156
<u>5</u> POLYFORMAL/DNPDI	-207	1.35	224.2	302.6	157
HNPDI DIOL/ <u>2</u> COPOLYFORMAL/TDI	-487	1.30	215.8	280.5	138
HNPDI DIOL/ <u>2</u> COPOLYFORMAL/DNPDI	-493	1.30	220.9	287.1	142
HNPDI DIOL/OFH DIOL COPOLYFORMAL/TDI	-679	1.52	219.8	334.1	200
HNPDI DIOL/OFH DIOL COPOLYFORMAL/DNPDI	-682	1.52	225.2	342.3	206
GAP NITRATE (500)	+182	1.30	219.7	285.6	141
GAP AZIDE (500)	+555	1.25	220.1	275.1	129


\*DNPDI = 3,3-Dinitropentane-1,5-diisocyanate  
HNPDI DIOL = Hexanitrodioxadiazapentadecanediol (6)  
OFH DIOL = Octafluoro-1,6-hexanediol

\*\*calculated

ABA Block Copolymer Synthesis. - In an initial reaction scheme for the synthesis of ABA triblock copolymers, a polyformal of the tetranitrotridecane-diol 5 ( $M_n \approx 9000$ ) was used as soft block, and was end-capped with excess TDI. The product was subsequently reacted with (a) methanol, (b) a monofunctional Poly(dioxolane/trioxane) copolymer (PDT) provided by Dr. Lillya from the University of Massachusetts, and (c) docosanol.

The product of the reaction with methanol gave a <sup>1</sup>H NMR spectrum (Fig. 16) supportive of the expected structure. Docosanol and especially PDT reacted more slowly and the initial products obtained contain unreacted starting material, as indicated by GPC and <sup>1</sup>H NMR analysis before and after solvent extraction. Since they exhibit some degree of elasticity, some triblock formation must have occurred, however.

5 Polyformal + TDI (excess)  $\longrightarrow$

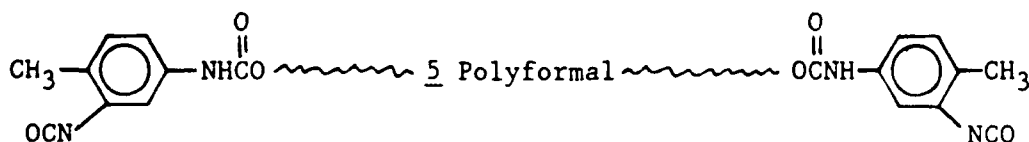

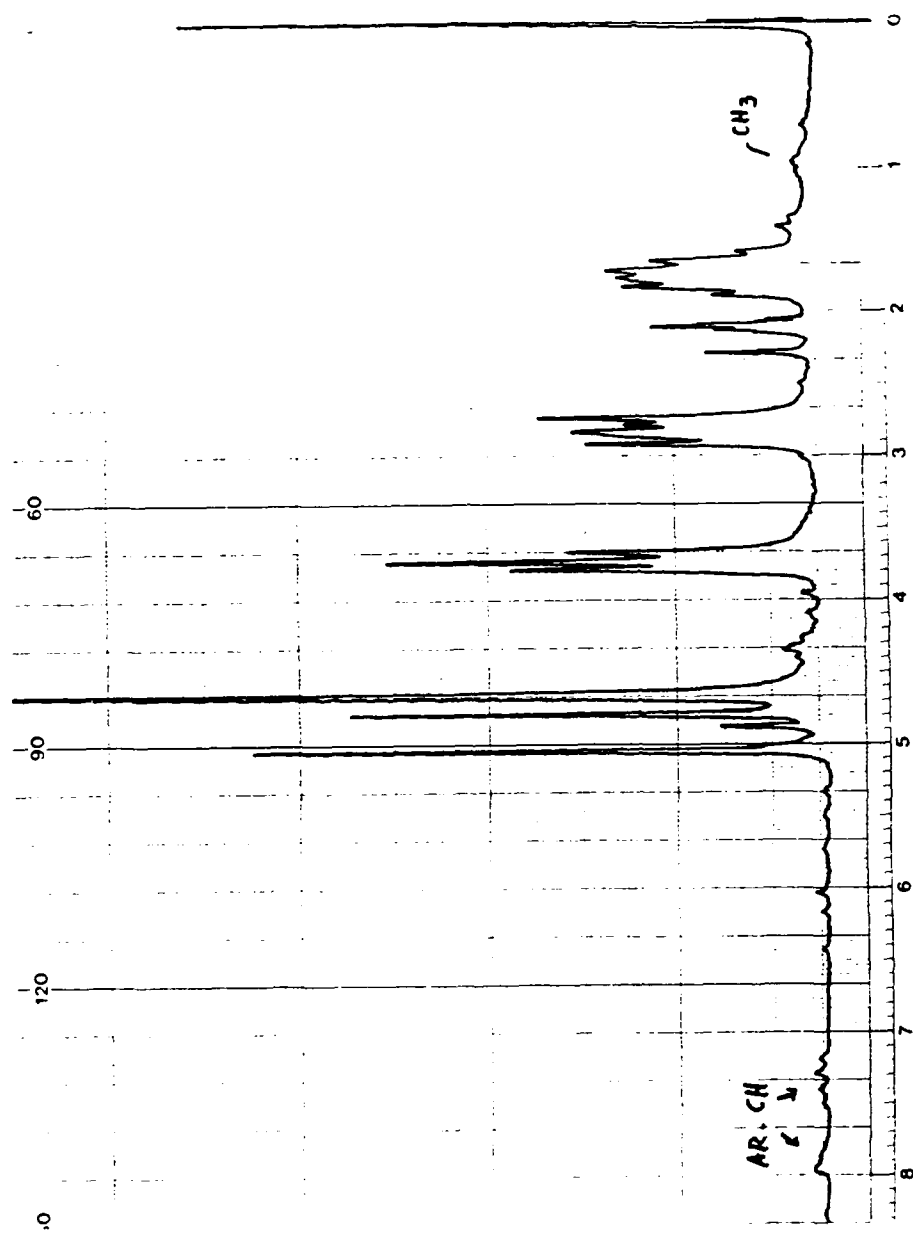


Fig. 16  $^1\text{H}$  NMR Spectrum of a Poly(5 formal) after End-capping with TDI and Reaction with Methanol



Table 3. ABA Polymers by Reaction of 13 with Polyformals of 5; Ratio 2:1

Polymer Number	Polyformal of <u>5</u> ( $\bar{M}_n$ )*	Wt% of <u>13</u> in final product	$\bar{M}_n$ **	$T_G^\dagger$ (°C)	$T_M^{\dagger\dagger}$	Characteristics (at room temp.)	GPC/DSC Fig. No.
1	9000 (11,500)	8.3	13,000	4	-50	elastic; not tough	17,18
2	7600 (7800)	11.7	(8,600)			elastic; tough	19
3	7600 extended w. TDI	8.5	16,500	-2	-50	elastic; tough	20,21
4	4460	18.0	(5500)	-	-	plastic; tough	22
5	4460 extended w. TDI	10.0	(10,000)	-	-	elastic; tough	23
6	4460 extended w. TDI	8.5	(11,500)	-	-	elastic; tough	24
7	4460 extended w. TDI	5.4	(18,500)	-	-	elastic; not tough	25

\*Estimated from the GP chromatogram; values in parentheses determined by GPC/viscosimeter method

\*\*No. 1 and 3 determined by GPC/viscosimeter method, others estimated from the GP chromatogram

$^\dagger$ by DSC

Visual inspection indicated that all polymers in Table 3 melted in the range 60-70°C, while the DSCs for polymers 1 and 3 (Figs. 18 and 21) show endothermic transitions over a wider and lower temperature range. Polymers 1, 2, and 4, which have soft blocks without additional urethane moieties, have low melt viscosities and flow readily when molten. The others are more viscous and resemble more the  $(AB)_N$  polymers prepared earlier by chain-extension of soft blocks with diisocyanates. Thus, it appears that the presence of many urethane groups in the polymer may be undesirable from viscosity considerations. The polymers prepared are being characterized more fully.

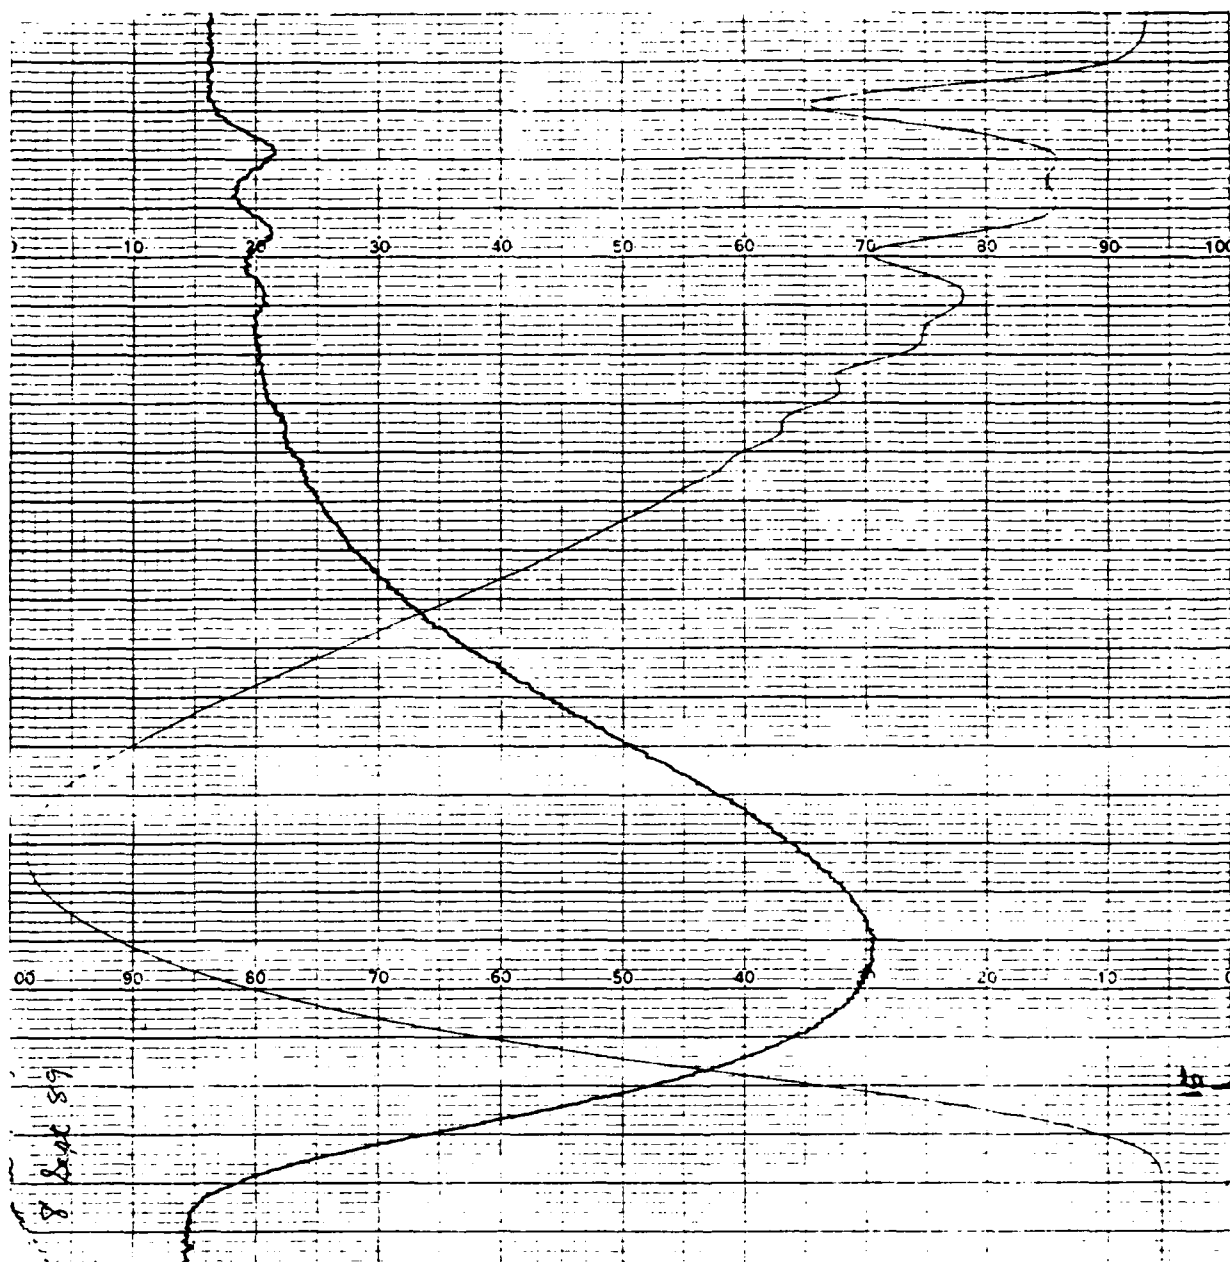


Fig. 17 GPC Chromatogram of ABA Block Polymer from Poly(5 formal),  $\bar{M}_n \sim 9000$ , and Isocyanate 13



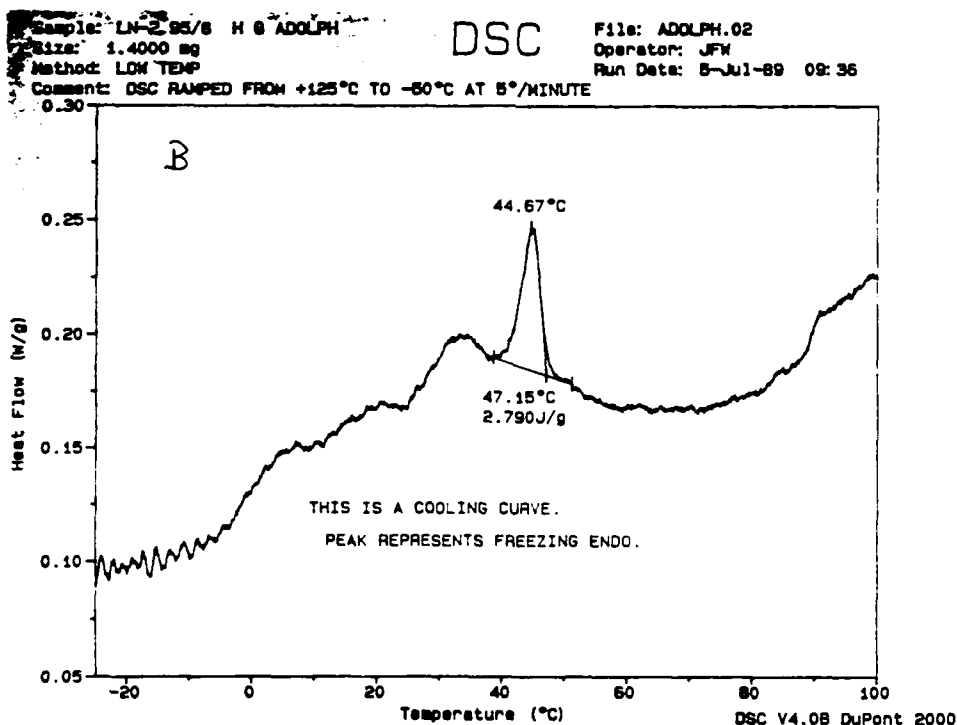
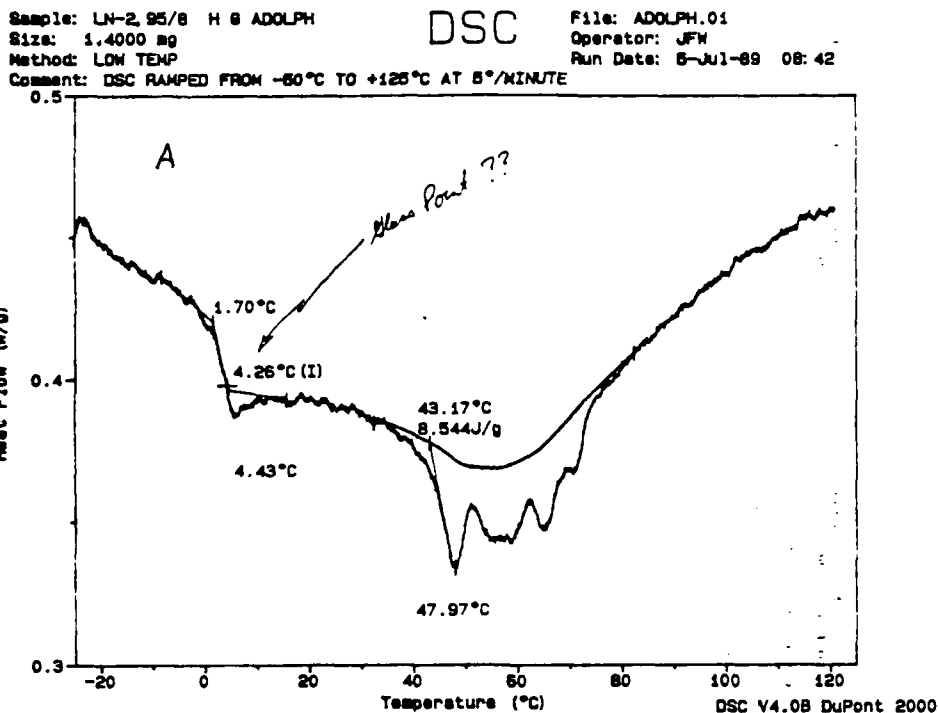


Fig. 18 DSC Traces for ABA Block Polymer from Poly(5 formal),  
 $M_n$  9000, and Isocyanate 13; (A) heating, (B) cooling

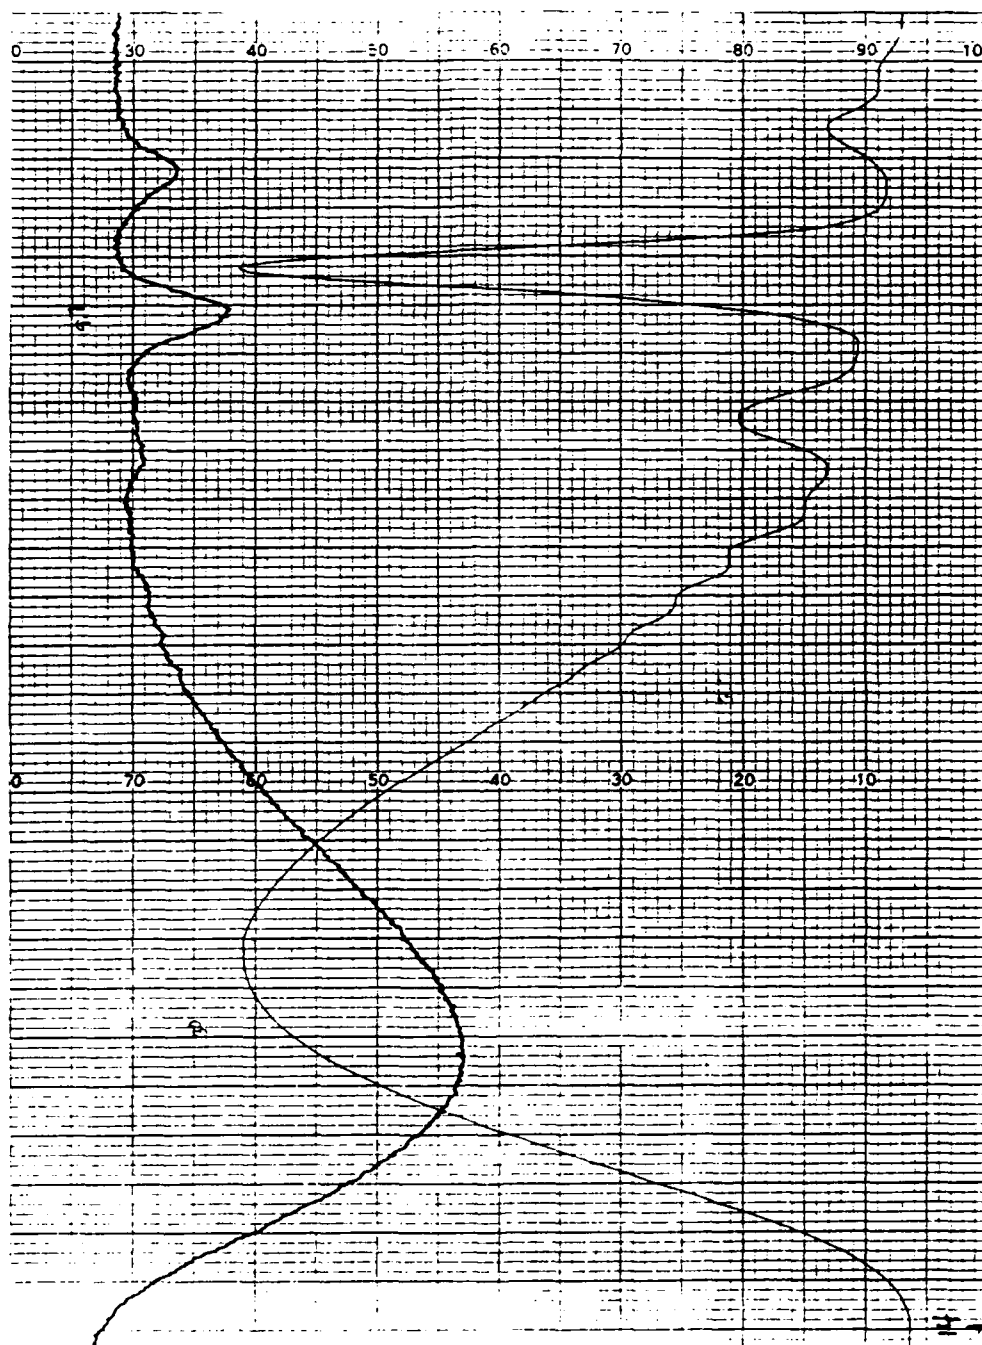


Fig. 19 GP Chromatogram of ABA Block Polymer from Poly(5 formal),  $\bar{M}_n \approx 7600$ , and Isocyanate 13

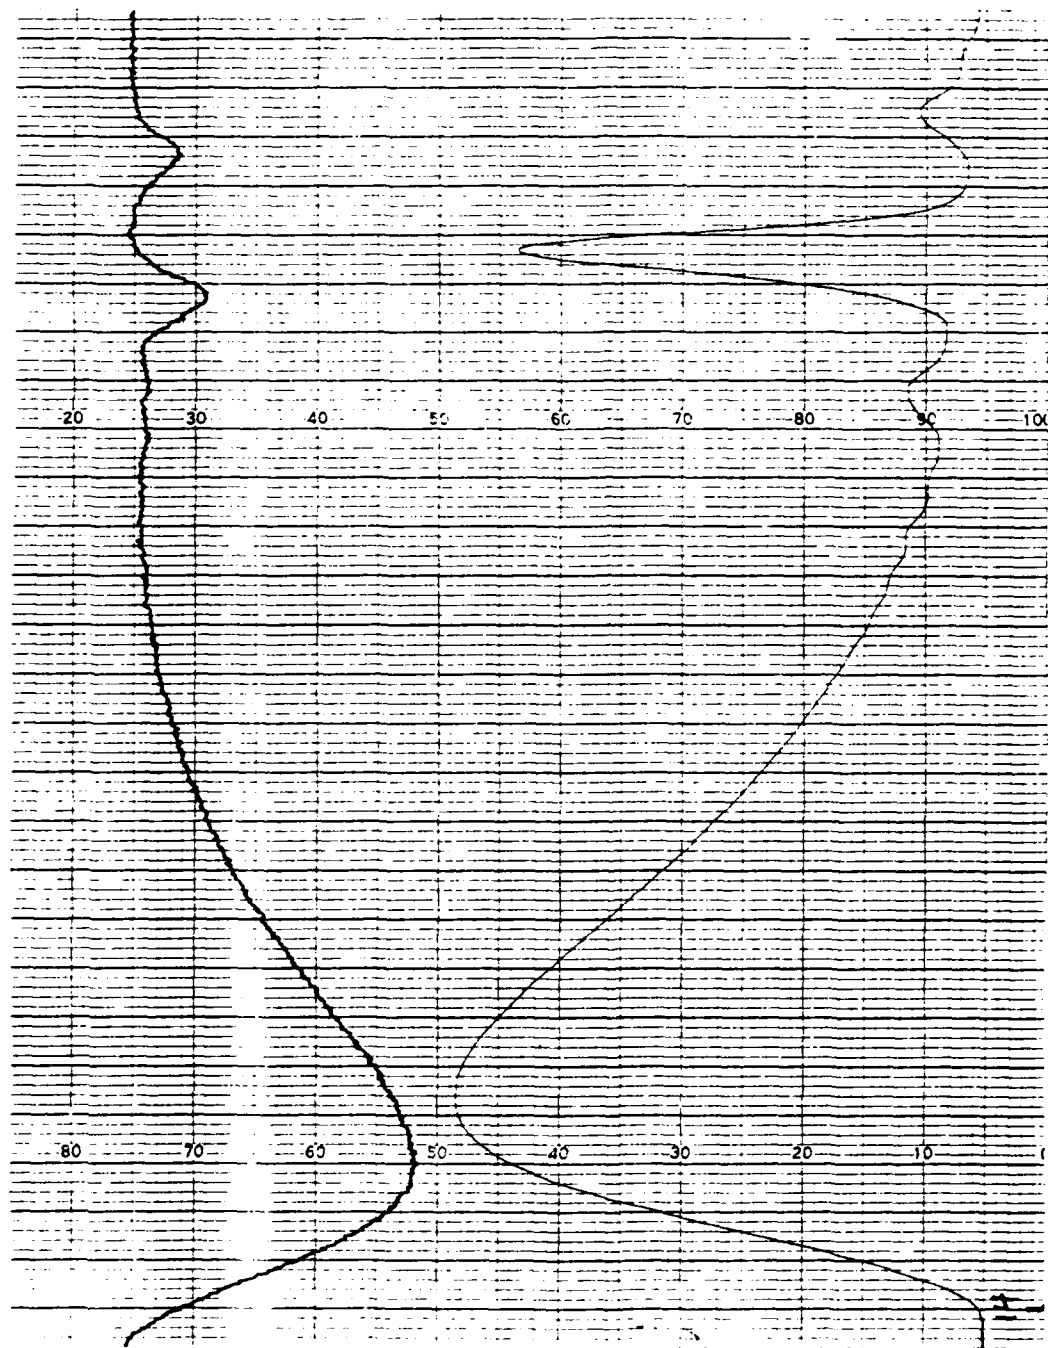



Fig. 20 GPC Chromatogram of ABA Block Polymer from Poly(5 formal),  $\bar{M}_n$  7600, TDI, and Isocyanate 13

Method: LOW TEMP WARM UP

Run Date: 7-Jul-89 09:56

Comment: NORMAL DSC RAMPED FROM -50 TO 150°C AT 5°/MIN

0.12

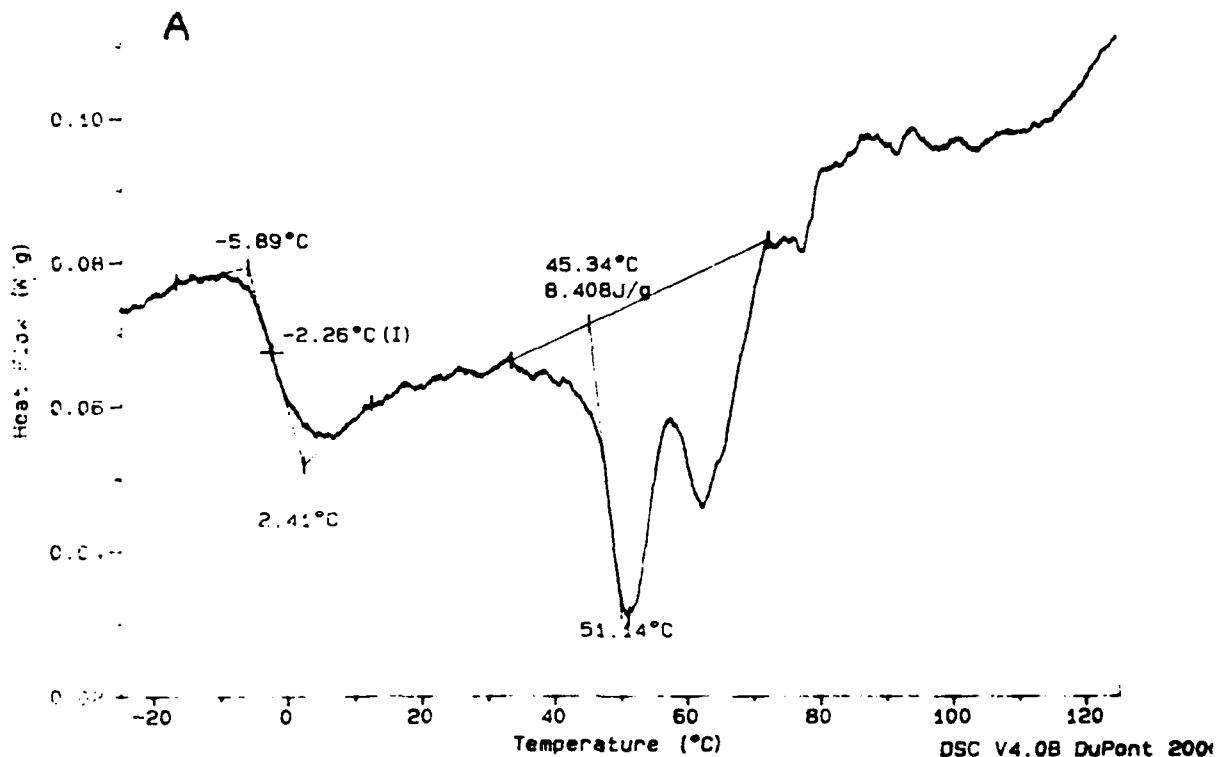

Method: COOLING CURVE

Run Date: 7-Jul-89 10:39

Comment: NORMAL DSC RAMPED FROM -50 TO 150°C AT 5°/MIN

0.35

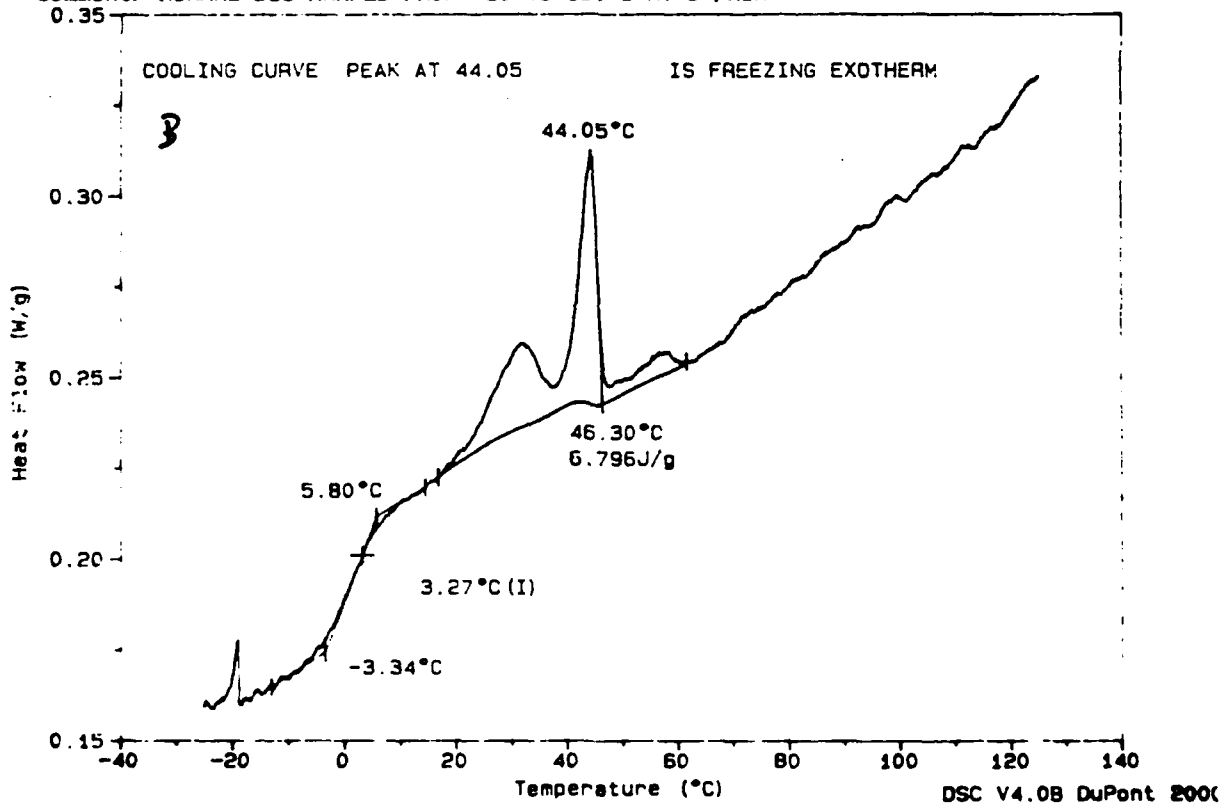


Fig. 21 DSC Traces for ABA Block Polymer from Poly(5 formal),  
 $\bar{M}_n$  7600, TDI, and Isocyanate 13; (A) heating, (B) cooling

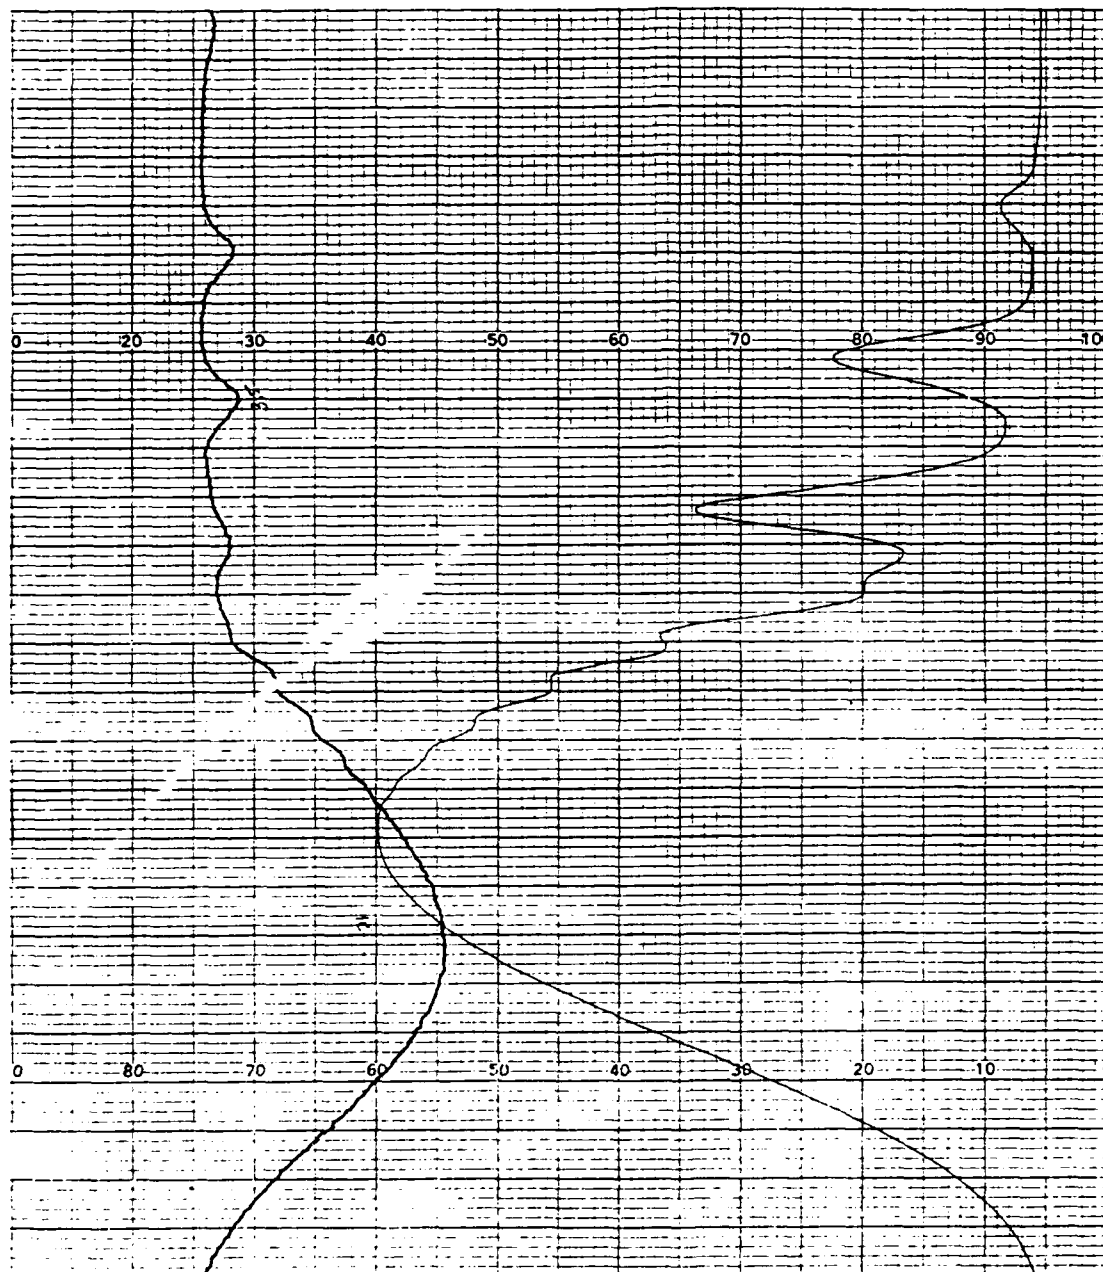


Fig. 22 GPC Chromatogram of ABA Block Polymer from Poly(5 formal),  $\bar{M}_n \approx 4460$ , and Isocyanate 13

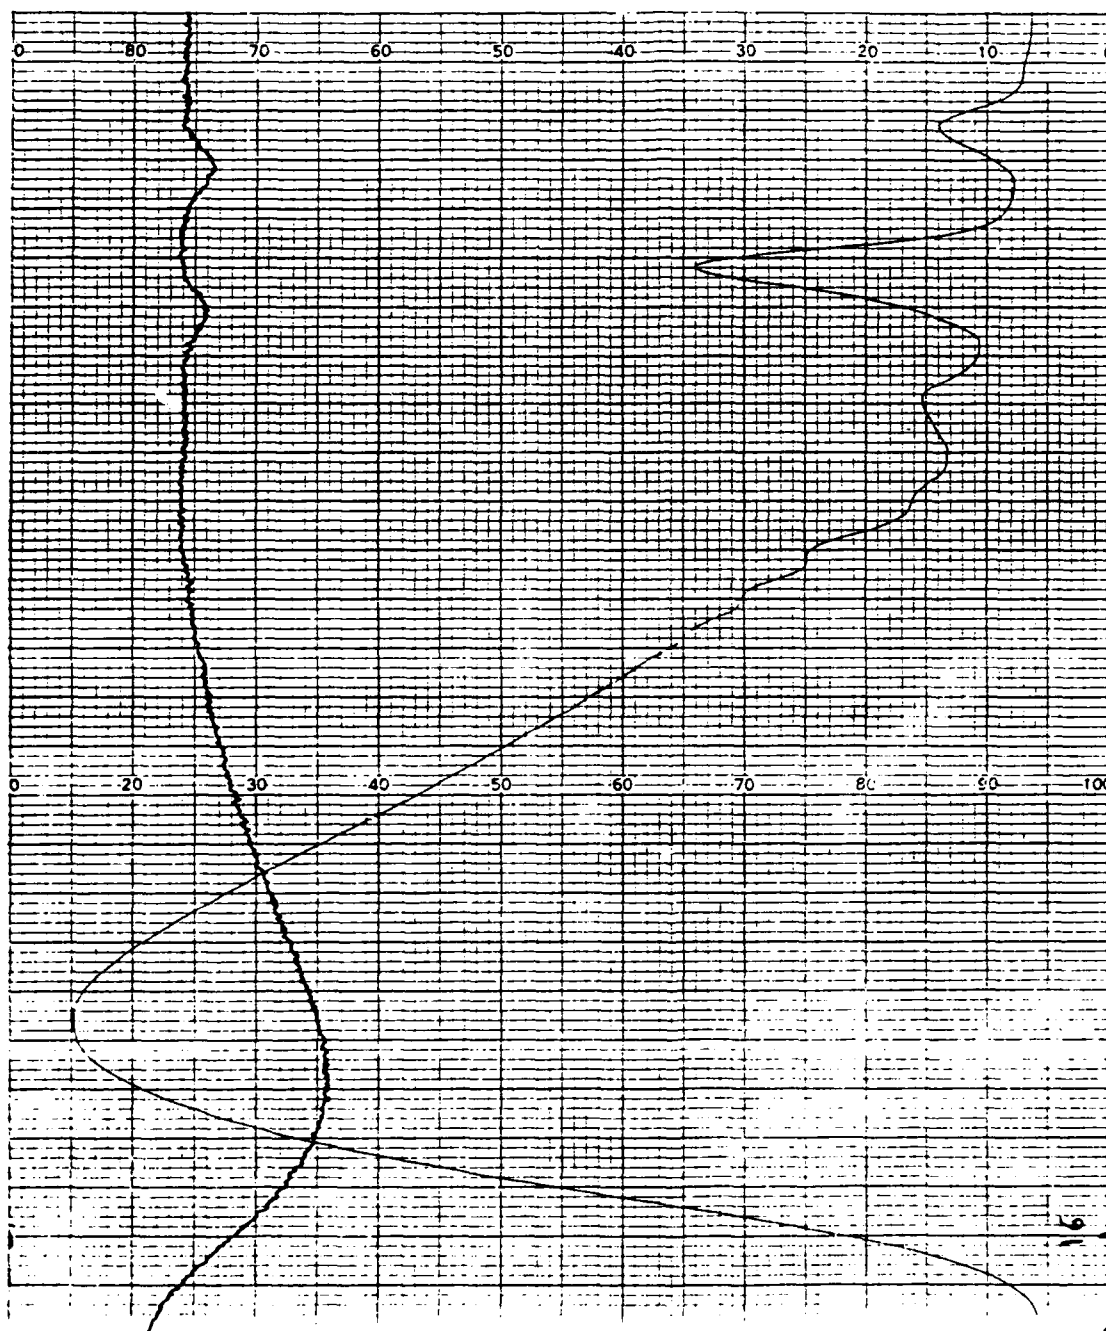


Fig. 23 GP Chromatogram of an ABA Block Polymer from Poly(5 formal),  $\bar{M}_n \approx 4460$ , TDI, and Isocyanate 13 (10% 13)

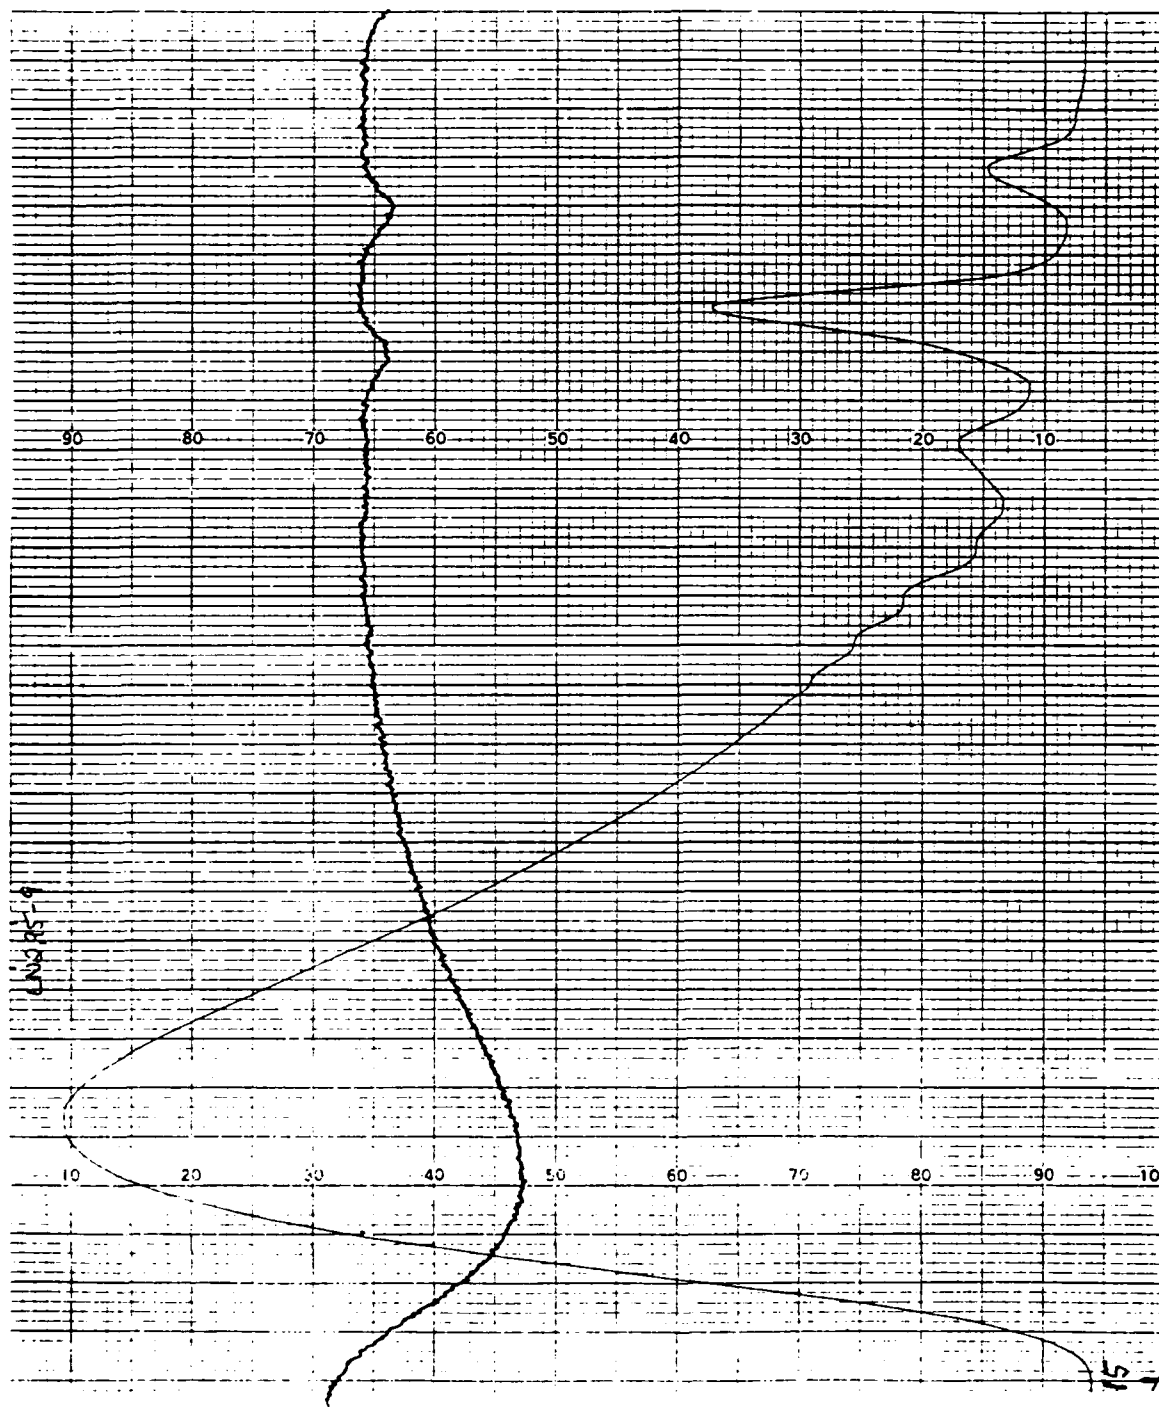


Fig. 24 GP Chromatogram of an ABA Block Polymer from Poly(5 formal),  $\bar{M}_n \approx 4460$ , TDI, and Isocyanate 13 (8.5% 13)


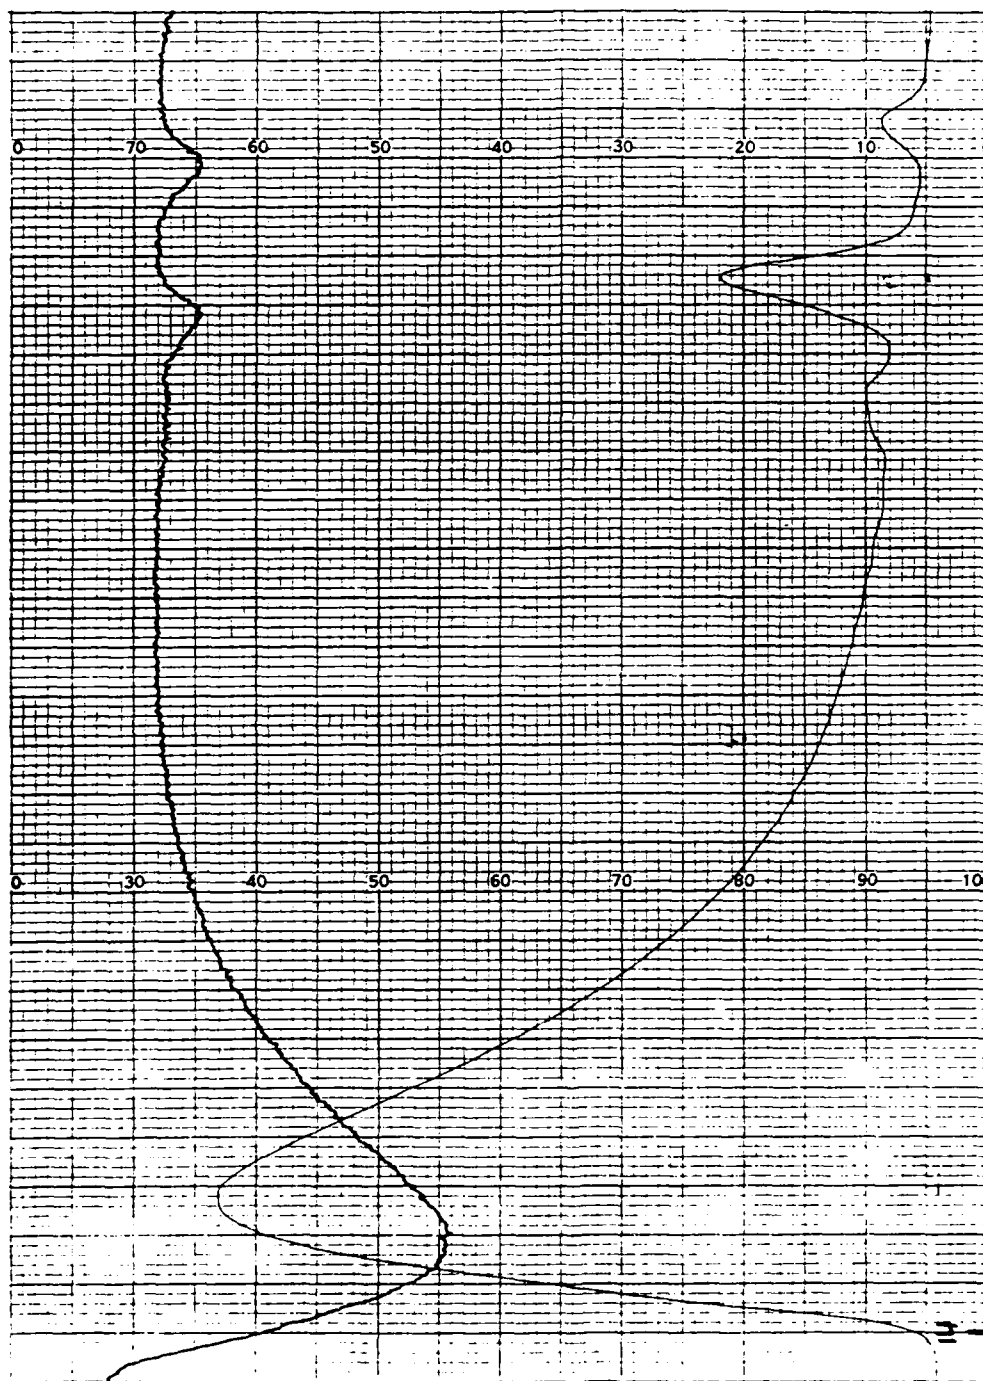


Fig. 25 GPC Chromatogram of an ABA Block Polymer from Poly(5 formal),  $\bar{M}_n \approx 4460$ , TDI, and Isocyanate 13 (5.4% 13)




Using analogous reaction conditions, 16 was reacted with the polyformal of 5 of  $M_n = 9000$  (ratio 2:1) to give a soft resin which contained unreacted 16 by GPC.<sup>n</sup> Further characterization is in progress.

In a similar fashion, PDT was reacted with TDI to the isocyanate 21. It was in turn reacted with the polyformal of 5 at 70° in sulfolane. The product, a soft, slightly elastomeric material which does not melt below 120°C, is currently being characterized.

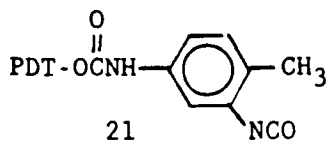

In order to assess possible effects of changes in the hard block structure on the ABA polymer properties, 5 polyformal ( $M_n \approx 7600$ ) was reacted with octadecyl isocyanate to the ABA polymer. This polymer (GPC, Fig. 26) was a resin with no elastomeric properties. Also, docosanoic azide (18) was heated in the presence of 5 polyformal to generate the isocyanate and the corresponding ABA polymer (22) (GPC, Fig. 27). This polymer was less elastomeric and softer than the corresponding polymer made with the docosanol/TDI adduct 13 as hard block. This indicates that the additional urethane groups in the polymer containing TDI contribute to its properties.

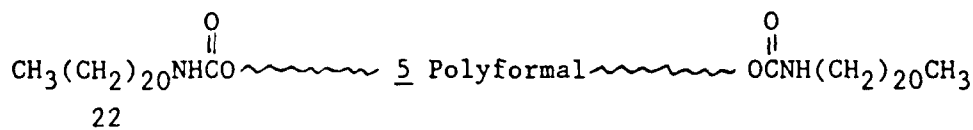

The hard blocks 13 and 16 were also reacted with the difunctional poly(AMMO) sample of OH equ. wt. 3125 obtained from Thiokol Corp. With 13, the product (GPC, Fig. 28) was initially waxy but on storage became somewhat elastomeric. The <sup>1</sup>H NMR spectrum (Fig. 29) indicates the presence of about 80% of the expected amount of docosyl groups in the polymer. With 16, reaction occurred also to give a polymer resin with no elastic properties. Characterization of this material is incomplete.

The above results indicate that a useful approach to prepare ABA block copolymers consisting of the linking of preformed hard and soft blocks has been identified. However, the properties of the polymers produced are not yet what is desired in terms of melt behavior, viscosity, and elasticity. It is believed that higher molecular weight hard and soft blocks are required to achieve acceptable properties. This will be the goal of our future research.

Polymer Characterization. - To further validate the new GPC method<sup>2</sup> to determine absolute number average molecular weight ( $M_n$ ) and intrinsic viscosity using the differential viscometer, the  $M_n$  of several additional standard samples of varying chemical structure and molecular weights ranging from 10,000 to 200,000 were determined. The results which are presented below compare favorably with the expected values.

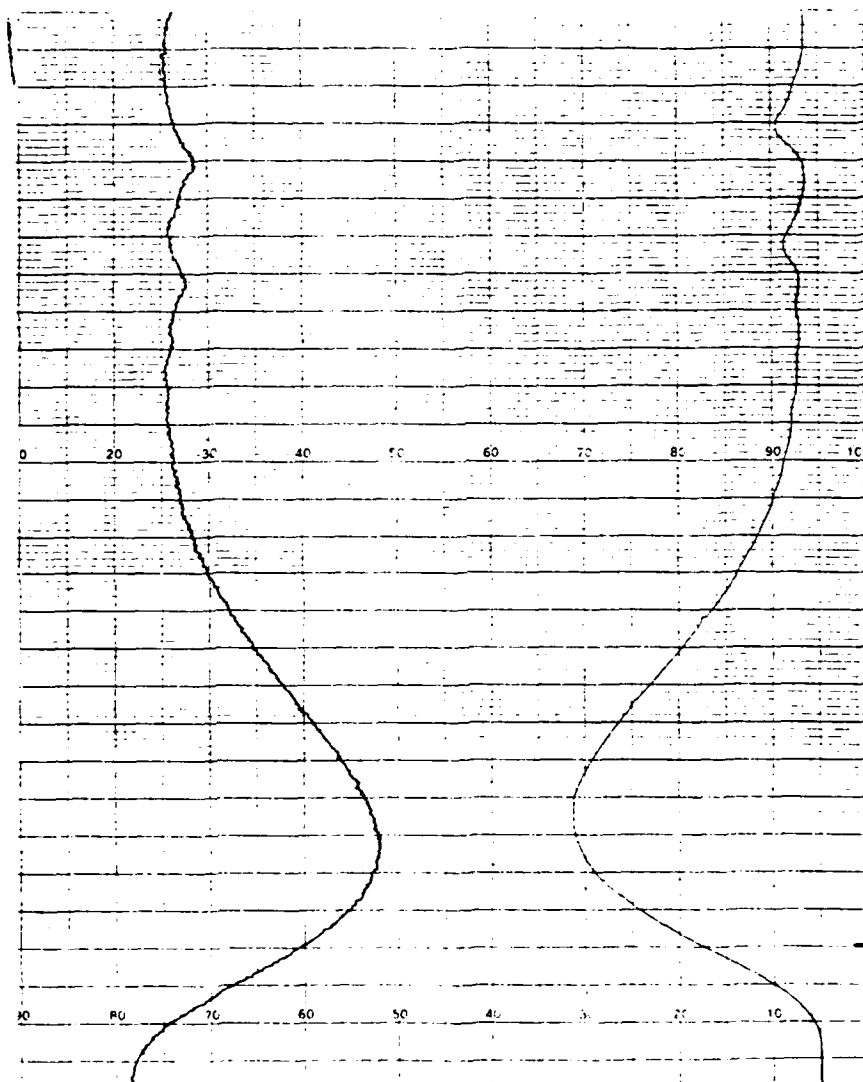


Fig. 26 GP Chromatogram of ABA Block Polymer from Poly(5 formal),  $\bar{M}_n \approx 7600$ , and Octadecyl Isocyanate

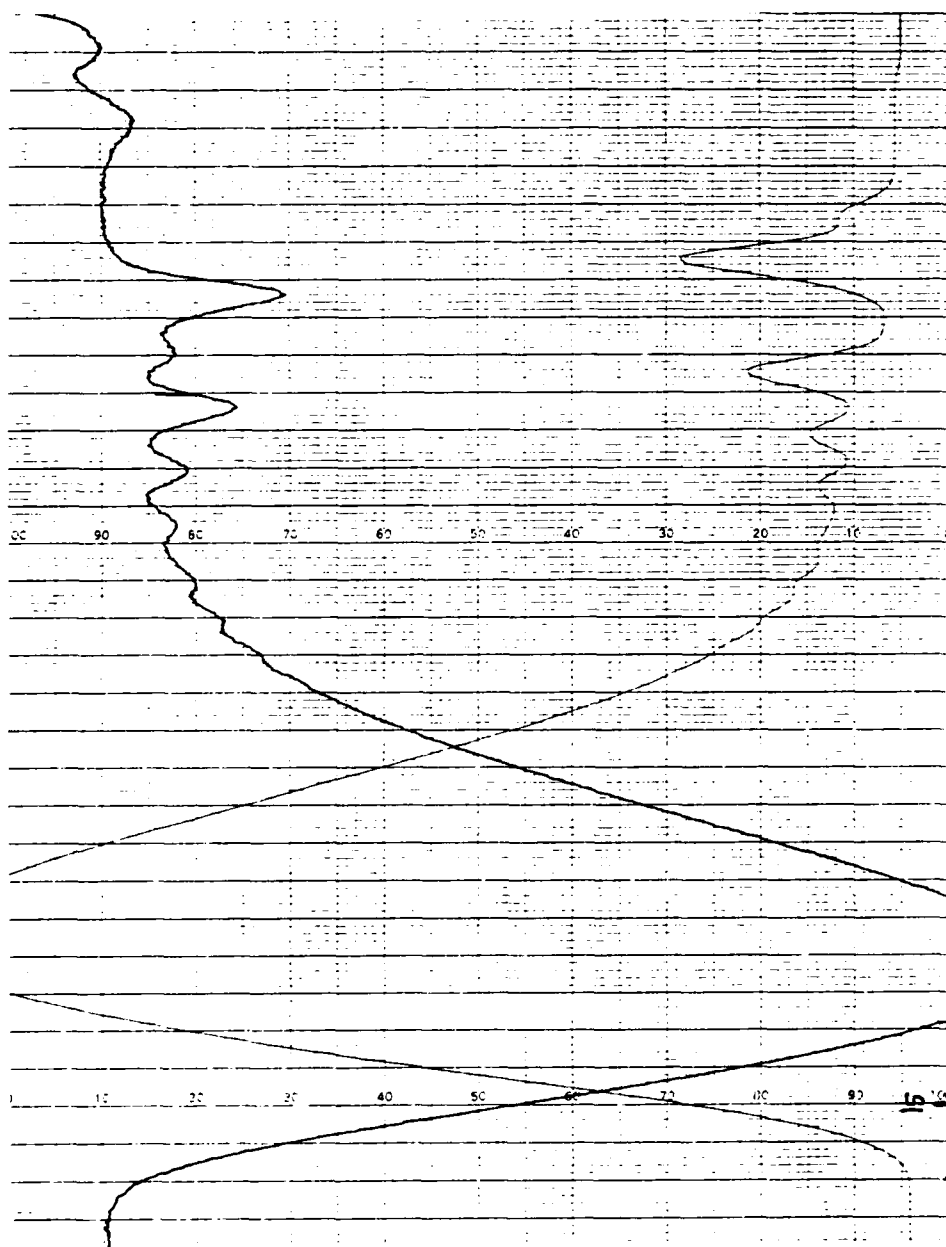


Fig. 27 GP Chromatogram of ABA Block Polymer from Poly(5 formal),  $\bar{M}_n \approx 7600$ , and Hereicosyl Isocyanate

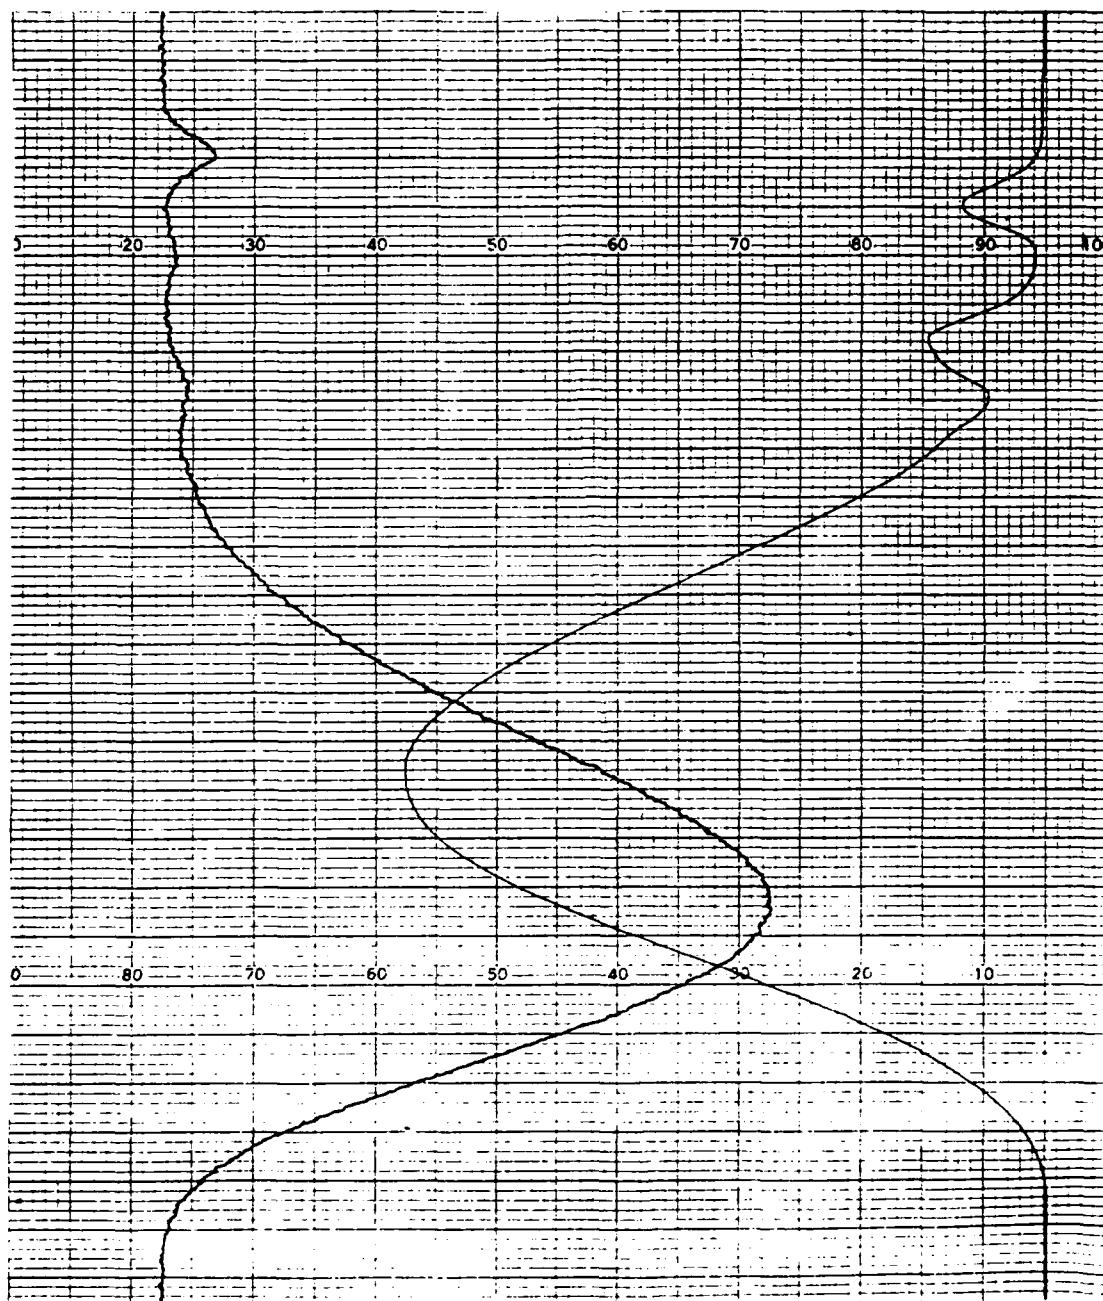


Fig. 28 GP Chromatogram of Product from Poly(AMMO) and 13

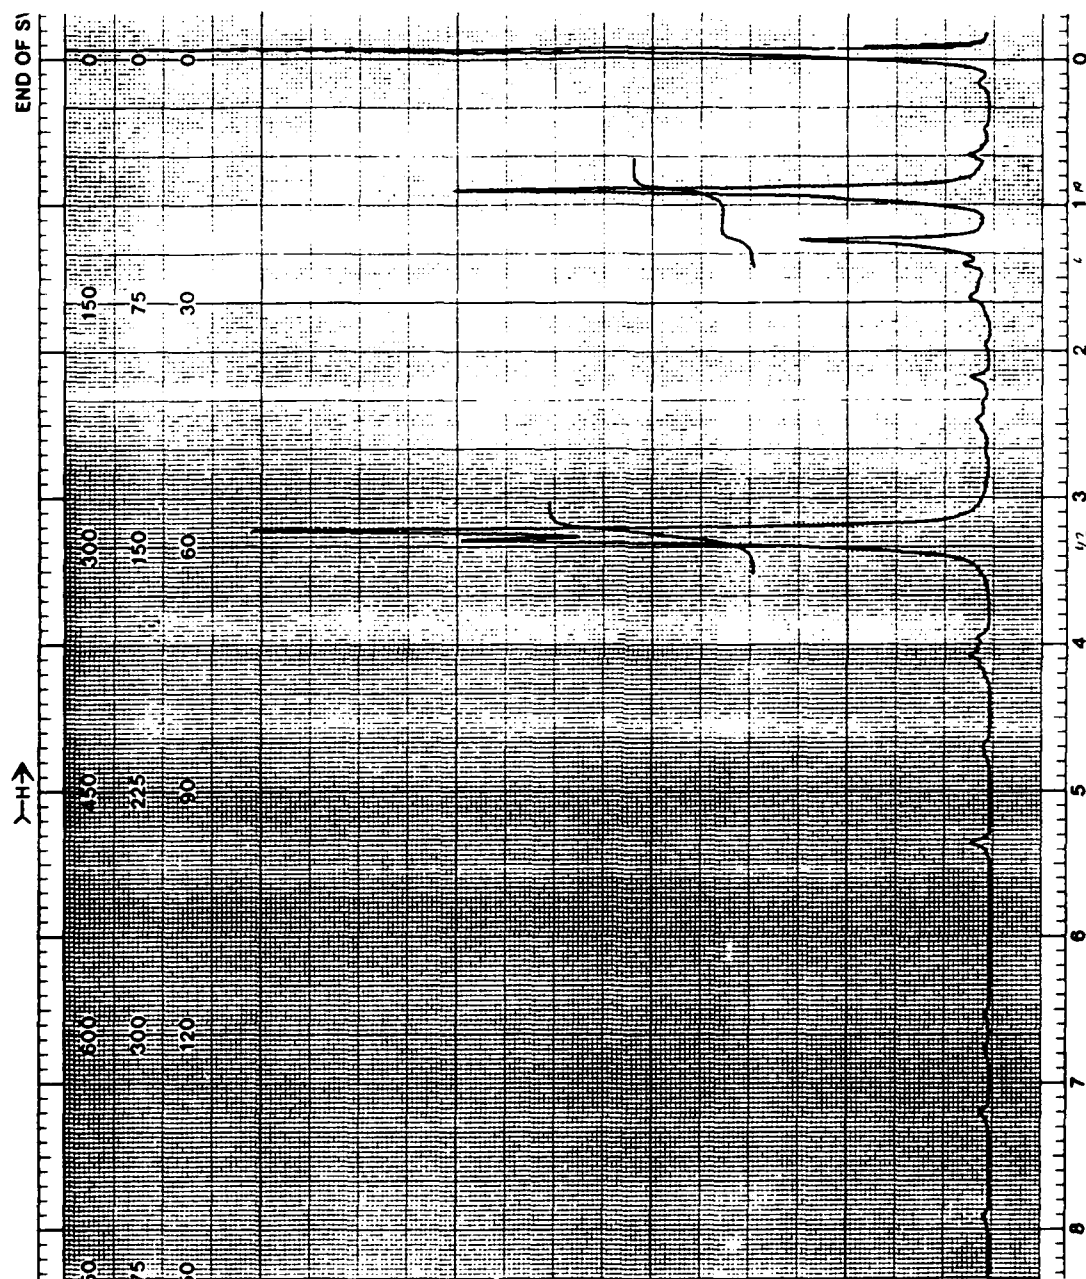


Fig. 29  $^1\text{H}$  NMR Spectrum of Product from Poly(AMMO) and 13

Table 4. Comparison of Reported and Measured Molecular Weights for Some Standard Polymer Samples

Polymer	Sample	$\bar{M}_n$		$[\eta]$ (mL/g)
		reported	measured	
polystyrene	PS-ALD	119,500	123,000	83.0
	PS-NBS	136,500	133,000	86.0
PMMA	PMMA-ALD	46,400	52,700	31.5
	PMMA-PSc1	63,000	66,897	44.3
	PMMA-PSc2	166,500	167,933	90.6
poly(butadiene)	PBD-PSc	139,500	138,428	219.0

In addition, the  $\bar{M}_n$ s of several mixtures of polystyrene, PMMA, poly(vinyl acetate), and poly(butadiene) were measured and compared with expected values. The results are presented in Table 5.

Table 5. Comparison of Calculated and Measured Molecular Weights for Some Polymer Mixtures\*

Polymer	Ratios	$\bar{M}_n$		$[\eta]$ (mL/g)	
		expected	measured	expected	measured
PS	homopolymer	137,000		86.0	
PMMA	homopolymer	46,400		31.5	
PVAC	homopolymer	89,900		68.5	
PBD	homopolymer	139,500		225.0	
PS:PMMA	70:30	85,400	86,500	72.3	68.1
	30:70	57,100	59,700	48.0	49.0
PS:PVAC	50:50	108,000	112,000	79.1	78.7
PMMA:PVAC	50:50	61,300	62,800	49.6	48.4
PS:PBD	50:50	137,000	144,000	157.0	148.0

\*PS is polystyrene, PMMA is poly(methyl methacrylate), PVAC is poly(vinyl acetate), and PBD is poly(butadiene).  $\bar{M}_n$ s of the homopolymer samples were supplied by the vendor.

The demonstrated ability to accurately measure the  $\bar{M}_n$ s and the intrinsic viscosities of polymer mixtures with differing chemical compositions, ratios, and molecular weight distributions confirms the universal application of the method. As a result, it is now possible to accurately determine the absolute  $\bar{M}_n$  and intrinsic viscosity of any polymer, copolymer, polymer blend or mixture. Mark-Houwink constants, chemical structure, chemical composition, and  $dn/dc$  values are not needed.

## EXPERIMENTAL SECTION

Melting points are uncorrected. Temperatures are in °C. Microanalyses are by Galbraith Laboratories, Knoxville, Tennessee. NMR spectra were obtained in part on a Varian EM-390 spectrometer, in part on a Varian XL-200 NMR spectrometer. Chemical shifts are in ppm relative to TMS internal standard. Silica gel was EM Kieselgel 60, 70-230 mesh, throughout.

Gel Permeation Chromatography, General Procedure. - Analyses of homopolymers and copolymers were performed using a Waters Model 6000A solvent delivery system, Model U6K injector, Model 440 ultraviolet (UV) absorbance detector, and Model R-401 refractive index detector. A Toyo Soda Micropak H-series guard column, 7.5 cm in length and 0.75 cm in diameter and three Toyo Soda Micropak TSK 3000H size exclusion columns, each 30 cm in length, with inside diameters of 0.75 cm, and packing pore sizes of 1500 Å were used. The eluant was deaerated Burdick & Jackson tetrahydrofuran with water content less than 0.01% in order to maximize peak resolution. Solvent flow was nominally 1.0 mL/min. Chart speed was 1.0 cm/min. Data were collected by a DIGITAL MINC microcomputer using a Chromatix CMX-10 dual channel interface module. Data reduction was performed with the Chromatix GPC2 software package. The sample (25-50 mg) was dissolved in 5 mL of deaerated tetrahydrofuran, and approximately 100 µL aliquot was filtered through a Millipore 0.5µ FH type filter and injected into the instrument. Calibration curves were constructed, whenever possible, using the peak positions and molecular weights of the resolved oligomers of each sample.

Some GPC experiments, and measurements of intrinsic viscosities using the newly developed methods, were carried out using a Waters model 6000A solvent delivery system connected to a Molytek Thermalpulse II flowmeter, and a Waters U6K manual injector. The detector used was a Viscotek model 100 Differential viscometer. The eluant was unstabilized tetrahydrofuran. The flow rate was nominally 1 mL/min. Intrinsic viscosities were determined both with GPC columns connected and without columns connected. GPCs were carried out using Toyo Soda, TSK, H series columns which were 30 cm in length. For polymers whose  $M_n$  were below 5000, three columns, each with packing pore size of 1500 Å (TSK-3000H) were used. For polymers whose  $M_n$  were above 5000, four columns with packing pore sizes of 1500 Å (TSK-3000H),  $10^4$  Å (TSK-4000H),  $10^5$  Å (TSK-5000H), and  $10^6$  Å (TSK-6000H), respectively, were used.

Data were collected using an IBM PC/AT microcomputer equipped with a Data Translation DT-22805 data acquisition board, and an 80287 math coprocessor chip. The data collection and data reduction software was written in-house using the ASYST version 2.10 scientific programming language. Number average molecular weights were determined using the new algorithm described earlier.<sup>2</sup>

Poly(2,2,9,9-tetranitro-4,4,5,5,6,6,7,7-octafluorodecane-1,10-diol formal). - Under a  $N_2$  atmosphere, .890 g of diol 1 (1.79 mmol) was stirred with 2.8 mL of dry sulfolane (4A sieves) and .46 mL of  $BF_3$  etherate until homogeneous. A solution of .054g of trioxane (1.8 mmol) in .5 mL of dry  $CH_2Cl_2$  (4A sieves) was added and the mixture was stirred at 22°C for -20 hrs. The reaction was quenched with 20 mL of water and stirred, after addition of 20 mL of ether, for 1 hr. The organic phase was separated and evaporated at 30°C/20 Torr.

The crude polymer was triturated with water at 40°C, adding a few mL of CH<sub>2</sub>Cl<sub>2</sub> when necessary for stirring, until no sulfolane could be detected in the <sup>1</sup>H NMR spectrum. The polymer was dissolved in ether, the solution was stirred overnight with -.25 g of silica gel, filtered, and stripped at 40°C/20 Torr. The polymer had a  $\bar{M}_n$  = 1000 with a yield of 82%.

Poly(2,2,11,11-tetranitro-4,4,5,5,6,6,7,7,8,8,9,9-dodecafluorododecane-1,12-diol formal).- Under a N<sub>2</sub> atmosphere, .98 g of diol 2 (1.6 mmol) was stirred with 2.0 mL of dry sulfolane (4A sieves) and .39 mL of BF<sub>3</sub> etherate until homogeneous. A solution of .05 g of trioxane (1.6 mmol) in .5 mL of dry CH<sub>2</sub>Cl<sub>2</sub> (4A sieves) was added and the mixture was stirred at 22°C for -20 hrs. The reaction mixture was quenched with 20 mL of water and 20 mL of CH<sub>2</sub>Cl<sub>2</sub> and was stirred for 1 hr. The organic phase was separated and evaporated at 60°C/20 Torr. The crude polymer was triturated with water at 40°C, adding a few mL of CH<sub>2</sub>Cl<sub>2</sub> when necessary for stirring, until no sulfolane could be detected in the <sup>1</sup>H NMR spectrum. The polymer was redissolved in CH<sub>2</sub>Cl<sub>2</sub>, the solution was stirred overnight with -.25 g of silica gel, filtered, and stripped (60°C/20 Torr). The polymer had a  $\bar{M}_n$  = 1500 with a yield of 73%.

Polyformal of Diol 3 (Fluorochem C<sub>7</sub>F<sub>14</sub> Diol).- To a solution of 5.00 g of diol 3 (11.4 mmol) and .341 g of trioxane (11.4 mmol) in 6.60 mL of dry sulfolane (4A sieves), under a N<sub>2</sub> atmosphere, was added .706 mL of SnCl<sub>4</sub>. The reaction mixture was stirred for 2-3 min. until gelation occurred; then the reaction was stored at room temperature for 24 hrs. The gel was broken up with a spatula, dissolved in 75 mL of ether, and stirred with 75 mL of water for 1 hr. The organic phase was separated and evaporated at 35°C/20 Torr. The crude polymer was dissolved in THF and the solution dripped into 250 mL of vigorously stirred water at -50°C. The polymer precipitated, while the THF was evaporated by means of an air stream. The water was decanted and the precipitated polymer was rinsed with fresh water. The sulfolane-free polymer was redissolved in 50 mL of ether and stirred with 50 mL of .1N H<sub>2</sub>SO<sub>4</sub> and 3 mL of 30% H<sub>2</sub>O<sub>2</sub> for 3 hrs. The organic phase was separated, stirred with 50 mL of 1% KOH and 1.5 mL of 30% H<sub>2</sub>O<sub>2</sub> for 3 hrs, separated, and washed with brine. The ether layer was then stirred with 15 mL of MgSO<sub>4</sub> for -3 hrs, filtered, and stirred overnight with 10 mL of silica gel. The silica gel was filtered off and the solvent was removed by heating at 20-65°C/20 Torr. The polymer had an estimated  $\bar{M}_n$  of 8-9000 with a yield of 88%.

Polyformal of Diol 4 (Fluorochem C<sub>13</sub>F<sub>25</sub> Diol).- To a solution of 1.00 g of diol 4 (1.35 mmol) and .040 g of trioxane (1.33 mmol) in 1.5 mL of dry sulfolane (4A sieves) under a N<sub>2</sub> atmosphere was added .32 mL of BF<sub>3</sub> etherate. The mixture was stirred at 22°C for 24 hrs. The polymer precipitated out of solution and was deposited on the sides of the flask. The liquid was decanted and the flask was rinsed with water. The polymer was dissolved in THF and dripped into 100 mL of vigorously stirred water at 60°C. The THF was evaporated in an air stream. The water was decanted and the remaining polymer was dried under vacuum (1 Torr) at 50°C over P<sub>2</sub>O<sub>5</sub>. The polymer had an estimated  $\bar{M}_n$  of 8000.

Scale up (60g batch) of Poly(4,4,10,10-tetranitro-6,8-dioxatridecane-1,13-diol formal).- Under a N<sub>2</sub> atmosphere, 57.60 g of diol 5 (.144 mol) and 4.40 g of



trioxane (.147 mol) was dissolved in 48 mL of dry sulfolane (4A sieves) and 4.5 mL of dry  $\text{CH}_2\text{Cl}_2$  (4A sieves). To the solution, cooled to 18-20°C, was added 8.48 mL of  $\text{SnCl}_4$ . The mixture was stirred at 20-22°C for 20-24 hrs, then quenched with 600 mL of water and 520 mL of  $\text{CH}_2\text{Cl}_2$  and stirred for 1 hr. The organic phase was separated and stirred with 600 mL of .1N  $\text{H}_2\text{SO}_4$  and 28 mL of 30%  $\text{H}_2\text{O}_2$  for 3 hrs, separated, then stirred with 600 mL of 1% KOH and 15 mL of 30%  $\text{H}_2\text{O}_2$  for 3 hrs. The organic phase was separated and washed with 600 mL of brine, stirred with 45 mL  $\text{MgSO}_4$  for .5 hr, filtered, and evaporated at 45°C/20 Torr. The remaining liquid was triturated with 350 mL portions of water to remove most of the sulfolane. The crude polymer was dissolved in a minimum amount of  $\text{CH}_2\text{Cl}_2$  and loaded onto a silica gel column. The residual sulfolane, cyclic materials, and some low molecular weight materials were eluted with  $\text{CH}_2\text{Cl}_2$ . Lastly, the polymer was eluted with 30/70 THF/ $\text{CH}_2\text{Cl}_2$ . The polymer solution was stirred with 30 mL of silica gel for 48 hrs, filtered, and stripped (60°C/1 Torr). The polymer yield was ~70% with an estimated  $M_n$  of 8000.

Poly(hexane-1,6-diol azidoacetal). - A mixture of 1.59 g (10 mmol) of diethylazidoacetal, 1.18 g of hexane-1,6-diol (10 mmol), and 3 drops of  $\text{BF}_3$  etherate was stirred at room temperature for 24 hr, then heated to 60°C for 24 hr with intermittent application of aspirator vacuum to remove ethanol formed. The mixture was cooled in ice water, and 0.1 mL of  $\text{BF}_3$  etherate was added dropwise. Then, heating at 60°C and intermittent application of vacuum was continued for 2 days. The polymer was cooled, diluted with dichloromethane, the solution washed with water, and dried ( $\text{MgSO}_4$ ). The solvent was removed under vacuum. The product was a resin at room temperature.

Poly(3,5,5,11,11,13-hexanitro-3,13-diaza-7,9-dioxapentadecane-1,15-diol formal-co-hexane-1,6-diol formal), Monomer Ratio 7:3. - Under a  $\text{N}_2$  atmosphere, 2.128 g of diol 6 (4.092 mmol), .207 g of diol 8 (1.75 mmol), and .175 g of trioxane (5.83 mmol) were dissolved in 2.0 mL of dry sulfolane (4A sieves) and 1.0 mL of dry  $\text{CH}_2\text{Cl}_2$  (4A sieves) with slight warming. The mixture was cooled to 18-20°C and .35 mL of  $\text{SnCl}_4$  was added. The mixture was stirred overnight at 22°C for 20-24 hrs, then was quenched with 20 mL of water and 15 mL of  $\text{CH}_2\text{Cl}_2$  and was stirred for 2 hrs. The organic phase was separated, stripped (60°C/20 Torr), and triturated with water until no sulfolane could be detected in the  $^1\text{H}$  NMR spectrum. The copolymer was redissolved in  $\text{CH}_2\text{Cl}_2$  and stirred with 5 mL of silica gel overnight, filtered, and stripped at 55°C/20 Torr. The copolymer had an estimated  $M_n$  of 2400.

Poly(3,5,5,11,11,13-hexanitro-3,13-diaza-7,9-dioxapentadecane-1,15-diol formal-co-butane-1,4-diol formal), Monomer Ratio 7:30. - Under a  $\text{N}_2$  atmosphere, 2.128 g of diol 6 (4.092 mmol), .169 g of diol 9 (1.89 mmol), and .176 g of trioxane (5.87 mmol) were dissolved in 3.0 mL of dry sulfolane (4A sieves). The mixture was cooled in an ice bath and .6 mL of  $\text{BF}_3$  etherate was added. After stirring for 20-24 hrs at 20°C, the reaction was quenched with 30 mL of water and 25 mL of  $\text{CH}_2\text{Cl}_2$  and was stirred for 1 hr. The organic phase was separated and washed with 25 mL of brine. The solvents were evaporated (50°C/20 Torr) and the remaining liquid was triturated with water until no sulfolane could be detected in the  $^1\text{H}$  NMR spectrum. The sulfolane-

free copolymer was redissolved in  $\text{CH}_2\text{Cl}_2$ , the solution stirred overnight with 5 mL of silica gel, filtered, and stripped ( $55^\circ\text{C}/20$  Torr). The resulting copolymer had an estimated  $M_n$  of 1500.

4,7-Dinitro-4,7-diazadecanedioyl azide. - CAUTION: Acyl azides are sensitive explosives and must be handled with appropriate care. A mixture of 10 g of 4,7-dinitro-4,7-diazadecanedioic acid (34.0 mmol) and 60 mL of thionyl chloride was slowly heated to  $60^\circ\text{C}$  and stirred for 24 hrs. The reaction was cooled to room temperature. The pale yellow solution was further cooled in a dry ice/acetone bath and hexanes were added to precipitate the acid chloride. The solid was collected by suction filtration and washed with hexanes. The crude material was recrystallized from dry  $\text{CH}_2\text{Cl}_2$  (4A sieves), dried under vacuum, and stored over  $\text{P}_2\text{O}_5$ . 2.0 g of the acid chloride was again recrystallized in  $\text{CH}_2\text{Cl}_2$  under a  $\text{N}_2$  atmosphere, dried under vacuum, and then, under a  $\text{N}_2$  atmosphere, dissolved in 30 mL of dry  $\text{CH}_3\text{CN}$  (4A sieves). The solution was cooled in an ice bath, 2.0 mL of trimethylsilyl azide was added, the cooling was removed, and the mixture was stirred overnight at  $20^\circ\text{C}$ . The  $\text{CH}_3\text{CN}$  was evaporated without heating at 20 Torr to leave an oil which began to crystallize on standing or when seeded. (Seed crystals were obtained by evaporating a small aliquot of the  $\text{CH}_3\text{CN}$  solution and inducing the residual oil to crystallization by scratching)  $\text{CCl}_4$  was slowly added and crystallization continued overnight at  $0^\circ\text{C}$ . The white solid was collected by suction filtration and washed with a small amount of cold isopropyl ether. The acyl azide was dried under vacuum over  $\text{P}_2\text{O}_5$  and stored at  $5^\circ\text{C}$ . The melting point was  $79-81^\circ\text{C}$ .

3,6-Dinitro-3,6-diazaoctane-1,8-diol bis(chlorocarbonate), pyridine adduct (11). - Under a  $\text{N}_2$  atmosphere, 5.1 g of triphosgene (17.3 mmol) were dissolved in 19 mL of dry  $\text{CH}_2\text{Cl}_2$  (4A sieves). Added were 4.5 g of 3,6-dinitro-3,6-diazaoctane-1,8-diol followed by an additional 10 mL of dry  $\text{CH}_2\text{Cl}_2$  (4A sieves). The mixture was stirred for 10 min., but the diol remained mostly undissolved. The mixture was cooled in an ice bath to  $-5^\circ\text{C}$  and a solution of 4.2 mL of pyridine (52.0 mmol) in 20 mL of dry  $\text{CH}_2\text{Cl}_2$  (4A sieves) was slowly dripped in over a 45 min. period. When 70-80% of the pyridine solution had been added, the diol was dissolved; then a new precipitate began forming. The reaction was allowed to warm to room temperature and 15 mL of anhydrous hexane was added. The solid was filtered, washed with four 30 mL portions of 50/50  $\text{CH}_2\text{Cl}_2$ /hexane, and dried under vacuum over  $\text{P}_2\text{O}_5$ . The melting point was  $77^\circ\text{C}$ .

1:1 Adduct of Docosanol and Toluene-2,4-diisocyanate (13). - Under a  $\text{N}_2$  atmosphere, 5.00 g of docosanol (15.3 mmol) were dissolved in 25 mL of dry dichloroethane (4A sieves) at  $65^\circ\text{C}$ . After the addition of 6.55 mL of TDI (46.1 mmol) and 50  $\mu\text{L}$  of dibutyltin dilaurate, the mixture was stirred for 48 hrs. The reaction was cooled to room temperature and then further cooled in an ice bath. The solid was collected by suction under a blanket of  $\text{N}_2$  and was washed several times with dry, chilled dichloroethane. The product was dried under vacuum over  $\text{P}_2\text{O}_5$ . MP =  $84-85^\circ\text{C}$ .

Reaction of Docosanol/TDI adduct 13 with methanol and with 4,4,10,10-tetranitro-6,8-dioxatridecane-1,13-diol. - 1. A small amount of 13 was dissolved in a few mL of dry  $\text{CH}_2\text{Cl}_2$  (4A sieves) under a  $\text{N}_2$  atmosphere. After

the addition of -1 mL of methanol and 2-3  $\mu$ L of dibutyltin dilaurate, the mixture was warmed to 30°C and stirred overnight. The solvents were evaporated to yield a white solid (14) with a mp of 94-96°C.

2. Under a N<sub>2</sub> atmosphere, .40 g of isocyanate 13 (.80 mmol) and .16 g of diol 5 (.40 mmol) were dissolved in 3 mL of dry dichloroethane (4A sieves) at 50°C. Added were -5  $\mu$ L of dibutyltin dilaurate and the mixture was stirred for 24 hrs. The temperature was decreased to 35°C, 1 mL of methanol was added, and stirring was continued for 3-4 hrs. The reaction was cooled in an ice bath and the solid was collected by suction filtration and washed with cold dichloroethane. Obtained was a white solid (15) with a melting point of 117-119°C.

1:1 Adduct of 1H,11H,11H-eicosafuoroundecanol and Toluene-2,4-diisocyanate, (16).- 2.0g of alcohol (3.77 mmol) were dissolved in 10 mL of dry dichloroethane (4A sieves) at 65-70°C under a N<sub>2</sub> atmosphere. After addition of 1.60 mL of TDI (11.2 mmol) and -15  $\mu$ L of dibutyltin dilaurate, the reaction mixture was stirred for 24 hrs. The heating was removed and the reaction was allowed to cool to room temperature. The reaction mixture was further cooled in an ice bath and the white solid was collected by suction filtration under a N<sub>2</sub> blanket. The solid was washed several times with chilled dichloroethane, then dried under vacuum (1 Torr) over P<sub>2</sub>O<sub>5</sub>. The product (16) had a melting point of 94°C.

The functionality of the adduct was determined by <sup>1</sup>H NMR after reacting the isocyanate with methanol. A small amount of the isocyanate was dissolved in dry dichloroethane (4A sieves) at 35-40°C. After the addition of -.5 mL of methanol and 1-2  $\mu$ L of dibutyltin dilaurate, the mixture was stirred overnight, then stripped (65°C/20 Torr). Obtained was a white solid (17) with a melting point of 115°C.

Heneicosoyl azide (18).- Thionyl chloride (5 mL) was added to 0.75 g (2.202 mmol) of dosocanoic acid and the mixture was heated to reflux for 3.75 hr. The mixture was allowed to cool and excess thionyl chloride was removed under vacuum. Dichloromethane (5 mL) was added, the mixture was warmed to 35 mL to facilitate dissolution of the acid chloride, and was then returned to room temperature. Trimethylsilyl azide (0.279 g, 2.422 mmol) was added and the mixture stirred at 30° for 66 hr. Evaporation of volatiles at  $\leq$ 25°C gave 0.862 g of a cream colored powder, whose <sup>1</sup>H NMR spectrum indicated the presence of some unreacted acid chloride. Filtration of a dichloromethane solution through a column of silica gel (Kieselgel 60, EM) gave a fraction of 0.126 g of pure 18. <sup>1</sup>H NMR (CDCl<sub>3</sub>):  $\delta$  0.90 (s, 3), 1.37 (m, 40), 3.35 (t, 2) ppm.

Chain Extension of Poly(4,4,10,10-tetranitro-6,8-dioxatridecane-1,13-diol formal) with Diisocyanates.- A mixture of 2.24g of the poly(5 formal), M<sub>n</sub> = 4460, (0.502 mmol) and .09g of cubanediisocyanate (0.5 mmol) were dissolved in 6 mL of dry dichloroethane (4A sieves) under a N<sub>2</sub> atmosphere. 1-2  $\mu$ L of dibutyltin dilaurate was added and the mixture was heated to 35°C and stirred 20-24 hrs. After the addition of 1 mL of methanol, the stirring was continued for -16 hrs. The solvents were evaporated at 60°C/20 Torr.

The following (AB)N block copolymers listed in Table 1 were prepared by the same procedure:

poly(5 formal) ( $\bar{M}_n = 7600$ )/cubane diisocyanate  
poly(5 formal) ( $\bar{M}_n = 4500$ )/IPDI  
poly(5 formal) ( $\bar{M}_n = 7600$ )/IPDI  
poly(5 formal) ( $\bar{M}_n = 7600$ )/HMDI

Chain Extension of Poly(AMMO) with Toluene-2,4-diisocyanate. - A solution of 1.030 g of poly(AMMO),  $\bar{M}_n = 6250$ , (0.1648 mmol) in 3.5 mL of dry dichloroethane (4A sieves) under a  $N_2$  blanket was heated to 35°C. TDI (.027 mL, 0.19 mmol) and 3  $\mu$ L of dibutyltin dilaurate were added and the mixture was stirred for 24 hrs. After the addition of 1 mL of methanol, stirring was continued overnight. The solvents were evaporated at 60°C/20 Torr.

Endcapping of Poly(4,4,10,10-tetranitro-6,8-dioxatridecane-1,13-diol formal) with Toluene-2,4-diisocyanate. - Under a  $N_2$  atmosphere, 1.530 g of poly(5 formal),  $\bar{M}_n = 6250$ , (0.245 mmol) were dissolved in 4.0 mL of dry dichloroethane (4A sieves). After the addition of .104 mL of TDI (0.731 mmol) and 2  $\mu$ L of dibutyltin dilaurate, the mixture was heated to 35°C and stirred overnight. The reaction mixture was cooled to room temperature and triturated with 10 mL of anhydrous hexane, keeping a  $N_2$  blanket over the material at all times. To remove any residual unreacted TDI, the viscous resin was triturated 4 times with 8 mL portions of anhydrous hexane, adding 1-2 mL of dry dichloroethane (4A sieves) when necessary for stirring. The isocyanate endcapped resin was stored under  $N_2$ .

The functionality of the above product was determined by  $^1H$  NMR after reacting it with methanol: to a mixture of 3 mL of dry  $CH_3CN$  (4A sieves), .1 mL of methanol, and -2  $\mu$ L of dibutyltin dilaurate at 35°C, was added a small amount of the TDI endcapped polymer. The mixture was stirred overnight 20-24 hrs, then stripped at 60°C/20 Torr.

ABA Block Copolymer by Reaction of TDI-endcapped Poly(5 formal) with 1-Docosanol. - A solution of .515 g of TDI-endcapped poly(5 formal) (0.078 mmol) in 5 mL of dry  $CH_3CN$  (4A sieves) was prepared under a  $N_2$  atmosphere as described above. The solution was heated to 65-70°C and .056 g of 1-docosanol (0.17 mmol) and 1-2  $\mu$ L of dibutyltin dilaurate were added. The mixture was stirred for 3-4 days, then cooled to 35°C. Approximately 1 mL of methanol was added and stirring was continued overnight. The solvents were evaporated at 65°C/20 Torr.

ABA Block Copolymer by Reaction of Poly(5 formal) and Isocyanate 13. - Under a  $N_2$  atmosphere, 1.007 g of poly(5 formal),  $\bar{M}_n \sim 9000$ , (0.11 mmol) were dissolved in 4 mL of dry dichloroethane at 50°C. Added were .091 g of 13 (0.188 mmol) and -5  $\mu$ L of dibutyltin dilaurate, and the mixture was stirred for 48 hrs. The temperature was decreased to 35°C, and 1 mL of methanol was added. Stirring was continued overnight, then the solvents were stripped at 65°C/20 Torr.

Two other polymers in Table 3 were prepared using the same procedure:

poly(5 formal),  $\bar{M}_n = 7600$ /Docosan-ol-TDI adduct (13)  
poly(5 formal),  $\bar{M}_n = 4460$ /docosan-ol-TDI adduct (13)

ABA Block Copolymer by Reaction of Chain extended Poly(5 formal) with Isocyanate 13. - A solution of 1.5 g of poly(5 formal),  $\bar{M}_n = 7600$ , (0.197 mmol) in 5 mL of dry dichloroethane (4A sieves) was prepared at 35°C under a  $N_2$  atmosphere. .008 mL of TDI (0.0562 mmol) and -5  $\mu$ L of dibutyltin dilaurate were added, and the mixture was stirred overnight. The temperature was increased to 50°C and .140 g of isocyanate 13 (0.28 mmol) were added. The stirring was continued for 2-3 days. The temperature was decreased to 35°C, 1 mL of methanol was added, the mixture was stirred for 3-4 hrs, and was then stripped at 65°C/20 Torr.

The following ABA block copolymers from Table 3 were prepared using the same procedure, except the prepolymers were extended with different amounts of TDI:

poly(5 formal),  $\bar{M}_n = 4460$  extended with 0.016 mL TDI/g polymer to  $\bar{M}_n = 9000$ /Docosan-ol-TDI adduct (13)  
poly(5 formal),  $\bar{M}_n = 4460$  extended with 0.018 mL TDI/g polymer to  $\bar{M}_n = 10,500$ /Docosan-ol-TDI adduct (13)  
poly(5 formal),  $\bar{M}_n = 4460$  extended with 0.024 mL TDI/g polymer to  $\bar{M}_n = 17,500$ /Docosan-ol-TDI adduct (13)

ABA Block Copolymer by Reaction of Poly(5 formal) with Isocyanate 16. - A dry solution of .970 g of poly(5 formal),  $\bar{M}_n = 8000$ , (0.121 mmol) in 5 mL of dichloroethane (from a stock solution dried over 4A sieves) was heated to 55-60°C under a  $N_2$  atmosphere. Added were .172 g of isocyanate 16 (0.244 mmol) and 2-3  $\mu$ L of dibutyltin dilaurate. The solution was stirred for 24 hrs. The reaction temperature was decreased to 35°C, 10 drops of methanol were added, and stirring was continued for 3 hrs. The reaction was allowed to cool to room temperature, and the reaction mixture was dripped into -75 mL of methanol. The methanol was decanted from the precipitated polymer and the residual solvents were removed at 60°C/20 Torr.

ABA Block Copolymer by Reaction of Poly(5 formal) with Octadecyl Isocyanate. - Poly(5 formal) ( $\bar{M}_n \approx 7600$ , 1.38 g, 0.1816 mmol), 5 mL of dry dichloroethane (4A sieves), octadecyl isocyanate (0.1073 g, 0.364 mmol) and 1 drop of dibutyltin dichloride were heated to 50°C for 3 days. Methanol (0.25 mL) was added and heating was continued for 24 hr. Removal of solvents under vacuum gave the crude polymer.

ABA Block Copolymer by Reaction of Poly(5 formal) with Heneicosoyl azide. - Poly(5 formal) ( $\bar{M}_n \approx 7600$ , 2.32 g, 0.305 mmol), dichloroethane (5 mL, dried over 4A sieves), heneicosoyl azide (0.234 g, 0.64 mmol) and 1 drop of dibutyltin dichloride were heated at 60-65°C for 5 days, 0.25 mL of methanol was added and reaction was continued at 40°C for 2 days. The polymer, obtained by removal of solvents in vacuo, was more elastomeric than the polymer of the preceding procedure.

Reaction of Poly(AMMO) with Isocyanate 13.- A dry solution of .915 g of poly(AMMO),  $M_n = 6250$ , (0.1464 mmol) in 5 mL of dichloroethane (from a stock solution dried over 4A sieves) was heated to 55°C and .160 g of 13 (0.32 mmol) and 3  $\mu$ L of dibutyltin dilaurate were added. This mixture was stirred for 20-24 hrs, then the temperature was decreased to 35°C, 10 drops of methanol were added, and stirring was continued for 3 hrs. The heating was removed and the reaction mixture was dripped into -75 mL of methanol to precipitate the polymer. The methanol was decanted and the polymer was heated to 60°C/20 Torr to remove any residual solvents.

Reaction of Poly(AMMO) with Isocyanate 16.- A dry solution of .915 g of poly(AMMO),  $M_n = 6250$ , (0.1464 mmol) in 5 mL of dichloroethane (from a stock solution dried over 4A sieves) was heated to 55°C under a  $N_2$  atmosphere. .233 g of 16 and 3  $\mu$ L of dibutyltin dilaurate were added and the mixture was stirred for 20-24 hrs. The temperature was decreased to 35°C, 1 mL of methanol was added, and stirring was continued for -3 hrs. After cooling to room temperature, the reaction mixture was dripped into -75 mL of methanol to precipitate the polymer. The resulting polymer was heated to 65°C/20 Torr to remove any residual solvents.

## References

1. H. G. Adolph, J. M. Goldwasser, D. A. Cichra, L. A. Nock, and M. Chaykovsky, Naval Surface Warfare Center, "Synthesis of Energetic Single Phase and Multi-phase Polymers", Annual Progress Report for 1987, Office of Naval Research Contracts N00014-87-WX-24109 and N00014-87-WX-24177.
2. H. G. Adolph, J. M. Goldwasser, L. A. Nock, D. A. Cichra, Naval Surface Warfare Center, "Synthesis of Energetic Single Phase and Multi-phase Polymers", Annual Progress Report for 1988, Office of Naval Research Contracts 88-AF00001 and N00014-88-WX-24004, May 1989.

Distribution:

Office of Naval Research  
Code 1132P (R. S. Miller) (2 copies)  
Code 1113 (Chemistry Division) (1 copy)  
Arlington, VA 22217

Leonard H. Caveny  
SDIO/IST  
Pentagon  
Washington, D. C. 20301-7100

Defense Technical Information Center  
Bldg. 5, Cameron Station (12 copies)  
Alexandria, VA 22314

Director  
Naval Research Laboratory  
Code 2627  
Washington, D. C. 20375

A. L. Slavkosky  
Scientific Advisor  
Commandant of the Marine Corps  
Code RD-1  
Washington, D. C. 20380

Director  
U. S. Army Ballistic Research Lab  
DRXBR-IBD  
Aberdeen Proving Ground, MD 21005-5066

U. S. Army Research Office  
Chemical & Biological Sciences  
Division  
P. O. Box 12211  
Research Triangle Park, N. C. 27709-2211

U. S. Army Missile Command  
DRSMI-RKL  
Walter W. Wharton  
Redstone Arsenal, AL 35898

Johns Hopkins University  
Applied Physics Laboratory  
CPIA (T. W. Christian)  
Johns Hopkins Road  
Laurel, MD 20707



R. Anderson  
United Technologies  
Chemical Systems Division  
P. O. Box 50015  
San Jose, CA 94150-0015

Thomas Archibald  
Fluorochem, Inc.  
680 S. Ayon  
Azusa, CA 91702

M. Armstrong  
Massachusetts Institute of Technology  
Room 66-505  
Cambridge, MA 01239

M. Barnes  
Atlantic Research Corp.  
7511 Wellington Road  
Gainesville, VA 22065

K. Baum  
Fluorochem, Inc.  
480 South Ayon Avenue  
Azusa, CA 91702

Harry Blemquist  
Olin Ordnance  
Box 278  
Marion, IL 62959

Michael A. Bonanno  
U. S. Army Ballistic Research Laboratory  
Attn: SLCBR-IB-P  
Aberdeen Proving Ground, MD 21005

T. Boggs  
Naval Weapons Center  
Code 389  
China Lake, CA 93555

Jeff Bottaro  
SRI International  
Menlo Park, CA 94025

Joseph H. Boyer  
Univ. of New Orleans  
Chemistry Dept.  
Lakefront  
New Orleans, LA 70148

Robert Brown  
Mass. Inst. of Tech.  
66-352  
Cambridge, MA 02139

Lawrence Carosino  
Hercules Inc.  
Hercules Research Center  
Wilmington, DE 19894

Thomas E. Casti  
Hercules Inc.  
Hercules Research Center  
Wilmington, DE 19894

James C. W. Chien  
Dept. of Polymer Sci. & Engr.  
University of Massachusetts  
Amherst, MA 01003

C. Coon  
Lawrence Livermore National Lab  
P. O. Box 808  
Livermore, CA 94550

Richard Costin  
Sartomer Company  
3801 West Chester Pike  
New Towne Square, PA 19073

John Crissman  
A209 Polymer Bldg.  
National Institute of Standards and  
Technology  
Gaithersburg, MD 20899

Joseph C. Crowley  
Lockheed Palo Alto  
Research Laboratory  
3251 Hanover Street  
B204/D9350  
Palo Alto, CA 94304

T. F. Davidson  
Vice President Technical  
Thiokol Corp.  
Aerospace Group  
3340 Airport Road  
Ogden, UT 84405

Roger W. Day  
Olin Research Center  
350 Knotter Drive  
Cheshire, CT 06410

D. Dillehay  
Thiokol Corp.  
Longhorn Division  
Marshall, TX 75670

Philip Eaton  
University of Chicago  
5735 S. Ellis Avenue  
Chicago, IL 60637

R. A. Earl  
Hercules, Inc.  
Magna, UT 84109

L. C. Estabrook, P. E.  
Thiokol Corp.  
P. O. Box 30058  
Shreveport, LA 71130

John Fisher  
Naval Weapons Center, Code 3853  
China Lake, CA 93555

Richard Fletcher  
Aerojet  
P. O. Box 15699C, Bldg. 05025  
Sacramento, CA 95812

M. B. Frankel  
Rockwell International  
Rocketdyne Division  
6633 Canoga Avenue  
Canoga Park, CA 91303

R. Geisler  
AFAL  
DY/MS-24  
Edwards AFB, 93523

Richard Gilardi  
Naval Research Laboratory  
Code 6030  
Washington, D. C. 20375

W. H. Graham  
Thiokol Corp.  
Huntsville Division  
Huntsville, AL 35807-7501

B. David Halpern  
Polysciences, Inc.  
Paul Valley Industrial Park  
Warrington, PA 18976

C. M. Havlik  
O/83-10, B/157-3W  
Lockheed Missiles & Space Co., Inc.  
P. O. Box 504  
Sunnyvale, CA 94086

J. C. Hinshaw  
Thiokol Corp./WASATCH  
P. O. Box 524  
Mail Stop 244  
Brigham City, UT 84302

R. A. Hollins  
Naval Weapons Center  
Code 3853  
China Lake, CA 93555

Capt. Mark Husband  
AFAL/RKPA  
Edwards AFB, CA 93523

Pamela Kaste  
SLCBB-IB-P  
U. S. Army Ballistic Research Laboratory  
Aberdeen Proving Ground, MD 21005-5066

Freddy A. Khoury  
A209 Polymer Bldg.  
National Institute of Standards and  
Technology  
Gaithersburg, MD 20899

C. Sue Kim  
Department of Chemistry  
California State Univ., Sacramento  
Sacramento, CA 95819

M. K. King  
Atlantic Research Corp.  
5390 Cherokee Avenue  
Alexandria, VA 22312

Peter Kirschner  
Aerojet Tactical Systems  
Sacramento, CA 95813

Robert G. Leclerc  
Sartomer Company  
3801 West Chester Pike  
New Towne Square, PA 19073

Geoffrey A. Lindsay  
Naval Weapons Center  
Code 3858  
China Lake, CA 93555

George A. Lo  
Lockheed Palo Alto  
Research Laboratory  
B204/093-50  
Palo Alto, CA 94304

Robert D. Lynch  
Atlantic Research Corporation  
7511 Wellington Road  
Gainesville, VA 22065

Gerald E. Manser  
Aerojet Solid Propulsion Co.  
Bldg. 05025  
P. O. Box 15699C  
Sacramento, CA 95813

Gregory B. McKenna  
National Institute of Standards & Tech.  
Polymers Division  
Gaithersburg, MD 20899

Dennis G. Murrell  
Hercules  
Hercules Research Center  
Wilmington, DE 19894

Melvin P. Nadler  
Naval Weapons Center  
Code 3851  
China Lake, CA 93555

Boris D. Nahlovsky  
Aerojet Tactical Systems  
P. O. Box 13400  
Sacramento, CA 95813

Arnold T. Nielsen  
Naval Weapons Center  
Code 38503  
China Lake, CA 93555

R. Peters  
Aerojet Strategic Propulsion Co.  
Bldg. 05025 - Dept. 5400  
MS 167  
Sacramento, CA 95813

Gene Rothgery  
Olin Corporation  
350 Knotter Drive  
Cheshire, CT 06410

Joseph J. Rocchio  
U. S. Army Ballistic Research Lab  
SLCBQ-IB-P  
Aberdeen Proving Ground, MC 21013

John J. Rusek  
AFAL/RKPA  
Edwards AFB, CA 93523

David C. Sayles  
Ballistic Missile Defense  
Advanced Technology Center  
P. O. Box 1500  
Huntsville, AL 35807

Robert Schmitt  
SRI International  
333 Ravenswood Avenue  
Menlo Park, CA 94025

R. B. Steele  
Aerojet Strategic Propulsion Co.  
P. O. Box 15699C  
Sacramento, CA 95813

Carlyle B. Storm  
M-1 MS C920  
Los Alamos National Laboratory  
Los Alamos, MN 87545

E. S. Sutton  
Thiokol Corp.  
Elkton Division  
P. O. Box 241  
Elkton, MD 21921

G. Thompson  
Thiokol Corp.  
Wasatch Division  
MS 240 P. O. Box 524  
Brigham City, UT 84302

Lee J. Todd  
Dept. of Chemistry  
Indiana University  
Bloomington, IN 47405

R. S. Valentini  
United Technologies  
Chemical Systems Division  
P. O. Box 50015  
San Jose, CA 94150-0015

Robert B. Wardle  
Thiokol Corp./WASATCH  
Box 707 M/S 244  
Brigham City, UT 84302

Henry Webster, II  
Manager, Chemical Sciences Branch  
Code 5063  
Naval Weapons Support Center  
Crane, IN 47522

J. R. West  
Morton Thiokol, Inc.  
P. O. Box 30058  
Shreveport, LA 71130

John S. Wilkes, Jr.  
FJSRL/NC  
USAF Academy, CO 80840

Rodney L. Willer  
Thiokol Corp.  
Elkton Division  
P. O. Box 241  
Elkton, MD 21971

G. A. Zimmerman  
Aerojet Tactical Systems  
P. O. Box 13400  
Sacramento, CA 95813

P. Lilliya  
Dept. of Chemistry  
University of Massachusetts  
Amherst, MA 01003